

Fullerene-Driven Photocarrier Processes in Perovskite Solar Cells: Recent Advances

Muhammad Waqas¹, Dhruba B. Khadka^{2,*}, Abdul Haseeb Hassan Khan¹ and Ying-Chiao Wang^{1,*}

¹Department of Materials and Optoelectronic Science, National Sun Yat-sen University, Kaohsiung, 804, Taiwan, R.O.C.

²Photovoltaic Materials Group, Center for GREEN Research on Energy and Environmental Materials, National Institute for Materials Science (NIMS), 1-1 Namiki, Tsukuba, Ibaraki 305-0044, Japan

*Correspondence and requests for materials should be addressed to D. B. K. (email: KHADKA.B.Dhruba@nims.go.jp) and Y.-C. Wang (email: ycwang@mail.nsysu.edu.tw)

Abstract

This review highlights recent advances in elucidating the photocarrier dynamics of fullerenes in perovskite solar cells (PSCs). Fullerenes and their derivatives serve a critical role in facilitating charge transport, suppressing recombination losses, and enhancing device stability, with particular focus on their influence at the photocarrier level. The interfacial interactions between fullerenes and perovskite photoabsorbers are pivotal for efficient carrier extraction, where the distinctive electronic properties of fullerenes promote effective charge separation and transport. Recent spectroscopic developments have significantly deepened our understanding of charge generation, transport, and recombination mechanisms within PSC architectures. Moreover, functionalized fullerene derivatives have been strategically engineered to optimize energy level alignment, mitigate interfacial losses, and improve overall photovoltaic performance. These advancements collectively contribute to the development of more efficient and stable PSCs, driving progress toward next-generation solar energy technologies with enhanced photocarrier dynamic performance.

Keywords: Perovskite solar cells; fullerenes, charge-carrier dynamics; electron transport material; interfacial modifiers.

1. Introduction

Organic-inorganic halide perovskite solar cells (PSCs) have emerged as a leading photovoltaic (PV) technology, demonstrating record-high power conversion efficiencies (PCEs)[1-3], along with the advantages of scalable processing[4] and low-cost fabrication routes[5, 6]. Despite these advancements, the commercialization of PSCs remains hindered by key challenges, including inefficient charge transport[7], significant recombination losses[8], and long-term operational instability[9]. Among the factors governing device performance, photocarrier dynamics-encompassing charge generation, separation, transport, and recombination-play a central role in determining overall efficiency. In this context, fullerenes have attracted considerable attention due to their high electron affinity[10, 11] and excellent charge mobility, positioning them as essential electron-transport materials (ETMs) for improving photocarrier behavior and device performance.

Fullerenes possess a unique cage-like structure[12] composed predominantly of hexagons[13], pentagons[14], and occasionally heptagons, with inherent molecular curvature[15] that critically influences their optical, electronic, and chemical properties[16-18]. This structural versatility allows for precise chemical functionalization, making fullerenes highly adaptable materials for optimizing PV performance in PSCs. Notably, fullerenes have demonstrated the ability to effectively passivate defect states (DSs) at both perovskite interfaces[19] and grain boundaries[20], where the formation of fullerene-halide radicals plays a key role in suppressing deep-level trap states[21], which are major contributors to charge-carrier trapping and nonradiative recombination losses. Beyond defect passivation, fullerenes significantly enhance electron transfer kinetics, thereby reducing hysteresis and improving the dynamics of photogenerated charge carriers[22, 23]. Their relatively large molecular size enables them to physically occupy grain

boundaries, hindering halide ion diffusion and thus mitigating ion migration pathways[21, 24], a critical factor in improving operational device stability[25, 26]. Furthermore, chemical modification of fullerenes with polar functional groups such as hydroxyl[27], carboxyl[28], or amino moieties[29] has been shown to enhance solubility, environmental stability, and interfacial compatibility with perovskite layers-collectively contributing to finely tuned charge dynamics and improved device performance.

The incorporation of fullerene derivatives has played a pivotal role in advancing the efficiency of PSCs, with fullerene-based ETMs enabling PCEs of up to 22%[30]. Nevertheless, recent advancements employing non-fullerene ETMs have surpassed the 25% efficiency threshold[31], underscoring the rapid evolution and diversification of ETM materials in next-generation PSC architectures[31].

Functionalized fullerenes exhibit multifunctional properties that extend beyond their conventional role as ETMs. In particular, they contribute to defect passivation at the perovskite/ETM interface and within grain boundaries, thereby suppressing non-radiative recombination pathways and promoting improved perovskite crystallinity during film formation [32, 33]. The resulting enhancement in film uniformity not only facilitates more efficient light harvesting but also contributes to prolonged device operational lifetimes[34]. Moreover, fullerenes provide an effective barrier against moisture and oxygen ingress, addressing key environmental degradation pathways and significantly improving the long-term stability of PSCs under ambient conditions[30, 35].

Despite these advantages, challenges such as molecular aggregation[36] and residual ion diffusion[32] persist in fullerene-based electron transport layers. To address these limitations,

cross-linkable fullerene derivatives have been developed, forming robust molecular networks that suppress aggregation and act as effective barriers against ion migration-thereby enhancing both the efficiency and operational stability of PSCs[11]. This review summarizes recent progress in the application of fullerenes in PSCs, with a particular focus on the interplay between fullerene molecular structures and device performance. By examining the latest strategies in fullerene design and functionalization, we provide insights into the optimization of charge-carrier dynamics within perovskite architectures. Continued innovation in fullerene chemistry and its integration into PSCs holds substantial promise for advancing high-efficiency, stable, and commercially viable next-generation photovoltaic technologies.

2. Carrier Dynamics Regulation

In high-performance PSCs, charge transport layers (CTLs) play a pivotal role in device operation by: (1) facilitating efficient charge carrier extraction, (2) promoting the formation of high-quality perovskite films with reduced defect densities[36-38], and (3) enabling flexible device architectures. For instance, interface-engineered CTLs have enabled PSCs to achieve PCEs exceeding 23% on flexible polyethylene terephthalate (PET) substrates[39].

To achieve such performance, optimizing the interfaces between the ETM and perovskite, as well as between the perovskite and hole transport material (HTM), is essential for enhancing charge generation, promoting efficient extraction, and suppressing non-radiative recombination losses. These interface improvements are commonly realized through perovskite composition engineering, surface/interface passivation strategies-such as fullerene-based interlayers-and CTL bandgap tuning to ensure favorable energy-level alignment (ELA)[40, 41]. Furthermore, the internal electric field, generated by the ΔE between the highest occupied molecular orbital (HOMO)

level of the HTM and the lowest unoccupied molecular orbital (LUMO) level of the ETM[42], plays a crucial role in facilitating exciton dissociation at the respective interfaces. In well-optimized devices, this built-in potential enables charge separation efficiencies exceeding 90%, while also promoting the diffusion and separation of photo-generated carriers throughout the active layer. Thus, careful bandgap alignment at the ETM/perovskite/HTM interfaces is imperative to minimize energetic barriers and ensure efficient and balanced charge transport across the device[43, 44].

2.1 Device Structure

PSCs leverage perovskite materials' unique properties to convert light into electrical energy[45]. A typical device comprises an electrode supporting an n-type ETM, (compact or mesoporous), a perovskite light-harvesting layer, and a p-type HTM. Upon light absorption, the perovskite excites electrons to its LUMO, forming excitons that dissociate at the ETM/perovskite and perovskite/HTM interfaces (Figure 1a)[46]. Free electrons transfer to the ETM and holes to the HTM (Figure 1b), with selective transport reducing recombination. Electrons collect at the anode, flow through an external circuit, and recombine with holes at the cathode. The ETM selectively transports electrons while blocking holes, and conversely, the HTM transports holes while blocking electrons. This selective transportation ensures efficient charge separation and minimizes recombination losses. The free electrons are subsequently gathered at the anode, where they traverse an external circuit, thereby producing an electric current. Finally, at the cathode, the electrons recombine with holes, completing the circuit. The effectiveness of this process is significantly enhanced by the perovskite material long diffusion lengths (L) and high carrier mobilities ($\mu_{n,p}$), enabling efficient charge separation and transport. PSCs can be manufactured using two distinct methods. These methods vary based on the order of deposition for the materials

involved, either the ETM is applied first, or the HTL is applied first, (Figure 1(c,d)). The choice of method influences the overall performance and characteristics of the device. In the standard architecture for conventional NIP-type configurations, an n-type ETM is placed beneath an insulating light-harvesting layer, with a p-type HTL situated above it (Figure 1d)[46]. This arrangement forms an (ETM/perovskite/HTL) stack. Conversely, the inverted PIN-type architecture features a p-type HTL at the base, an insulating light-harvesting layer in the middle, and an n-type ETM on top, resulting in an (HTL/perovskite/ETM) configuration (Figure 1e). These two configurations will be conferred in the following section.

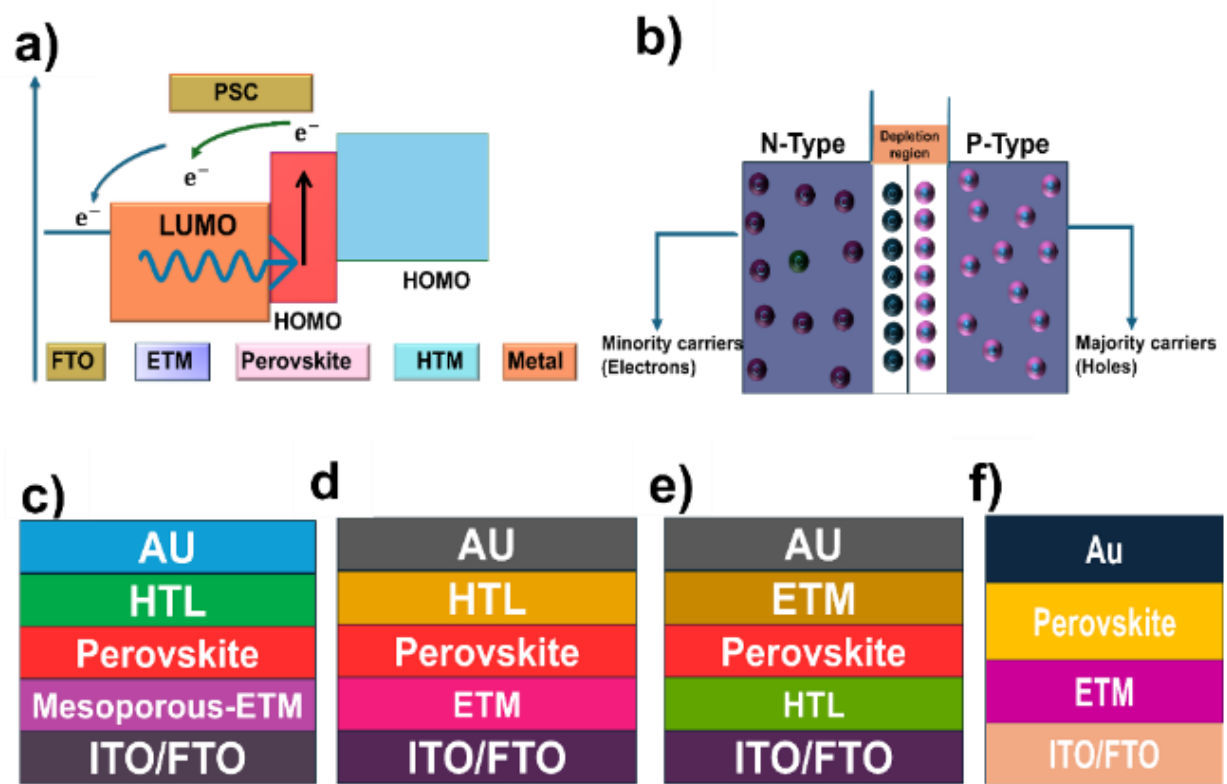


Figure 1. a) Working principle of PSC[47] , b) PN-junction[48], c) mesoporous configuration[49], d) NIP configuration, e) PIN configuration[50], and f) HTL-free PSC[51].

2.1.1 NIP Configurations

The NIP diode, characterized by its N-type (N), intrinsic (I), and P-type (P) layers, is a highly adaptable semiconductor device extensively employed in electronic and optoelectronic technologies[52]. Unlike conventional diodes, which contain only N-P junctions, the NIP diode includes a substantial intrinsic layer between the N-type and P-type regions[53]. This intrinsic layer is crucial for its unique operational characteristics, such as low capacitance and high-speed switching capabilities, making NIP diodes indispensable in high-frequency applications and photodetection.

Understanding the operation of an n-i-p diode requires a foundational knowledge of the photo-induced charge carriers interface[54]. The creation of the charge carrier junction in an NIP diode requires the doping of semiconductor material to establish regions with excess positive (P-type) and negative (N-type) charge carriers. The intrinsic (i) layer, undoped and positioned between these two regions, plays a pivotal role in the diode functionality. When a potential difference is applied across the NIP diode, the electric field spans the intrinsic region, resulting in the formation of an extensive depletion zone. This depletion region is essential for the diode high-speed switching and low capacitance, as it allows the diode to quickly respond to changes in the applied voltage without the significant charge storage issues found in conventional diodes. In photovoltaic applications, the width of the depletion region plays a key role in the PCE[55]. A narrow depletion region, often found in conventional diodes, poses several challenges[56]. Firstly, it leads to higher capacitance, which hampers the diode ability to operate effectively at high frequencies. Secondly, and more critically for photovoltaics, narrow depletion regions are less efficient in separating and collecting excitons generated under incident illumination[57]. This inefficiency in charge carrier separation results in lower responsivity and conversion efficiency,

ultimately limiting the effectiveness of PSCs relying on these diodes[58]. In contrast, the NIP diode's wide depletion region offers significant advantages for photovoltaic applications[59]. An extensive intrinsic region may lead to a slower response speed due to the increased distance for electrons and holes to travel and recombine[60].

2.1.2 PIN Configuration

The PIN structure, a variant of the NIP configuration, comprises layers arranged sequentially as a p-type layer, an insulating or intrinsic layer, and an n-type layer[61]. The intrinsic (i) layer plays a critical role in enabling efficient photon absorption and generating charge carriers[62]. The absorber materials that are composed of perovskite can effectively absorb a broad spectrum of photons that generate electron-hole pairs (excitons), which contribute to a PCE of 24%, as reported in Table 1. The layer quality impacts charge separation and transport, with advancements in perovskite synthesis enhancing crystallinity, reducing defect density, and enhancing stability, ultimately boosting the PCE and thermal stability of NIP PSCs[63].

Table 1. Device data of NIP[64, 65], PIN[66, 67], Mesoporous[68] and HTL-free configurations[69].

Device Configuration	Perovskite	ETM	HTM	PCE (%)	Stability
NIP	MAPbI ₃	TiO ₂	Spiro-OMeTAD	21-26.42	80%
PIN	FA _{0.90} MA _{0.10} PbI ₃	SnO ₂	NiO	23.1-26.14	85%
Mesoporous	(FAPbI ₃) _{0.97} (MAPbBr ₃) _{0.03}	TiO ₂	Spiro-OMeTAD	25.5	96.6%
HTL-free	Pb perovskite	TiO ₂		10-11	90%

2.1.3 HTL free PSCs

PSCs primarily rely on multiple CTLs, including ETMs and HTLs. The frequently utilized inorganic HTLs are 2,2',7,7'-tetrakis (N, N-p-dimethoxyphenylamino)-9,9'-spirobifluorene (Spiro-OMeTAD), polytriarylamine (PTAA), and Nickel oxide (NiOx), etc. These materials significantly contribute to the effective collection and transfer of charge carriers. However, the inclusion of HTLs introduces several challenges, including material instability which is a significant concern, as HTLs, particularly Spiro-OMeTAD, are susceptible to chemical and thermal degradation, which impacts device stability[70, 71], also NiOx, which is characterized by a high concentration of Ni^{3+} , can accept electrons from tin perovskites. This interaction facilitates the oxidation of Sn^{2+} to Sn^{4+} , which ultimately leads to diminished stability in Ni-based tin PSCs[69, 72]. Additionally, the hygroscopic nature of numerous HTL materials leads to moisture absorption from the environment, hastening the degradation of the light-harvesting layer[73, 74]. The low hole mobility of commonly used HTL materials further hampers efficient charge transport, reducing overall device performance[75]. Moreover, perovskites possess long carrier diffusion lengths, often exceeding several hundred nanometers[76]. These characteristics enable efficient charge separation and extraction within the light-harvesting layer, theoretically reducing the need for separate ETMs and HTLs[77].

Due to the bipolar nature and extended carrier diffusion length of perovskites, the presence of an ETM and an HTL is not essential for the mechanisms of charge separation and extraction. In an optimal configuration, as described by Chen et al., the light-harvesting layer alone would be sufficient to gather and transport charge carriers to the respective electrodes with minimal losses [78, 79]. This concept has led to the exploration of HTL-free PSC configurations (Figure 1f), aiming to simplify device architecture and reduce manufacturing costs.

In recent years, significant efforts have been directed toward the development of PSCs without the HTL layer[80]. Etgar et al. were the first to propose the successful fabrication of HTL-free PSCs, demonstrating that the $\text{CH}_3\text{NH}_3\text{PbI}_3$ (MAPbI₃) crystal could function both as a hole conductor and a light absorber, (Figure 2a). Zhang et al. improved the ELA by creating a layered perovskite structure composed of MAPbI₃/MAPbI_xBr_{3-x}. The valence band maximum (VBM) of MAPbI_xBr_{3-x} was 0.23 eV higher than that of MAPbI₃, facilitating hole extraction by reducing the energy barrier (Figure 2b). At the same time, the conduction band (CB) of MAPbI_xBr_{3-x} was found to be 0.25 eV higher than that of MAPbI₃ (Figure 2c), which hindered the electron transfer from the light-harvesting layers to the carbon electrode.

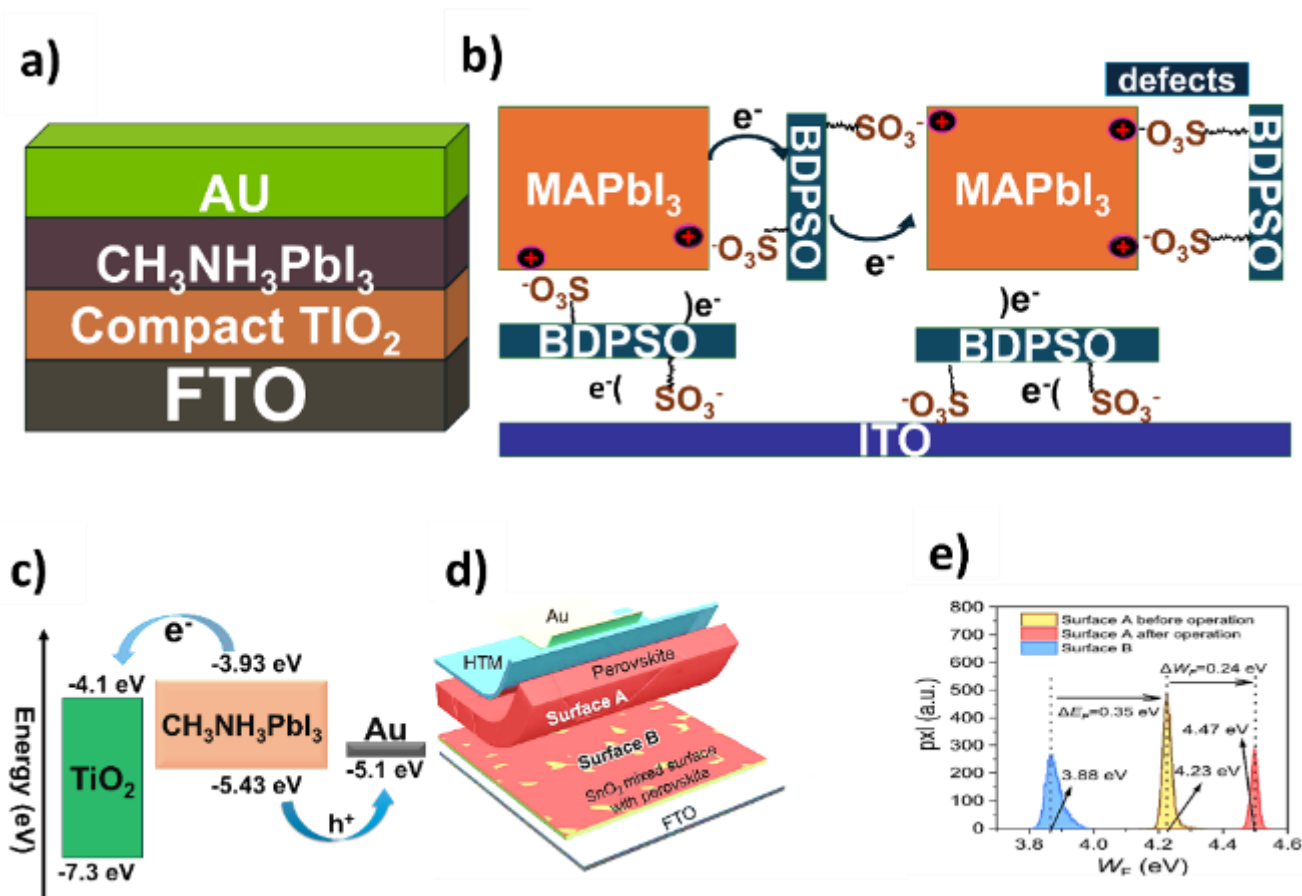


Figure 2. a) Device representation of HTL-free PSC[81]. b) A schematic representation depicting the influence of BDPSO dopants in HTL-free PSC[82]. c) Energy states diagram of HTL-free PSC, d) A schematic illustration of the separation at the buried interface of the PSC. The inset displays the use of a KPFM or AFM probe for measuring the work functions (WFs) of surface A and surface B[83]. e) The WF distribution of surface A before and after operation, compared with surface B, is presented the SnO_2 surface was modified with $-\text{C}_3\equiv\text{N}$ [84].

2.2 Charge transport layer Engineering

In PSC devices, the behavior of photoinduced excitons is predominantly governed by the attributes of the active layer [85]. Moreover, the performance of a PSC is contingent upon its proficiency in capturing incident photons, as well as the effectiveness of charge transport and collection at the corresponding electrodes[86, 87] Various elements that influence light propagation and charge transport within the device, such as energetic barriers at interfaces, the existence of defect states in the light-harvesting layer or adjacent functional layers, and parasitic absorption, will impose limitations on the overall performance of the device. Recently, the PCE of PSCs has witnessed advancements driven by the strategic implementation of interface engineering. This approach involves the incorporation of distinct interfacial materials between the ETM/HTL and perovskite active layer[41, 73]. The introduction of interfacial materials serves two primary functions: ELA and chemical modification.

2.2.1 Optimization of Energy Levels

To enhance the photoinduced charge carrier's dynamics in PSCs, carrier transport layers, such as the ETM and HTL, are typically incorporated on either side of the perovskite active layer. However, an energy level mismatch between the charge carrier transport layers and the perovskite can lead to energy losses at the interfaces. Thus, precise control of the interface ELA is essential for optimizing the photovoltaic parameters. Probing the ELA between the perovskite layer and the neighboring transport layers necessitates a detailed assessment of the energy level offset and the relative positions of their fermi energy levels (FEL). The electronic states offset at the interface play a critical role in affecting interfacial recombination and dynamics of Carrier infusion. The positioning of the FEL determines the alignment and extent of energy band bending at the interface,

which in turn influences the efficiency of charge carrier extraction. Moreover, the FEL of the perovskite and adjacent layers significantly affects the quasi-FEL splitting in PSCs, thereby influencing the maximum achievable photovoltage. Therefore, to attain the best possible performance from the device, it is essential to carefully evaluate these factors.

In PSCs, defect-assisted recombination primarily arises from Shockley-Read-Hall (SRH) recombination and interfacial recombination mechanisms, (Figure 3). These processes are critical in determining the overall efficiency of charge carriers [88, 89]. SRH recombination in light-harvesting layers is primarily instigated by the presence of uncoordinated ionic defects, which give rise to deep-level defect states. These DSs are energetically positioned within the bandgap and can capture free charge carriers, effectively impeding the charge dynamics, and thereby increasing defect-assisted recombination (Figure 3b). This process results in significant energy losses, as the trapped carriers recombine without contributing to photovoltaic output.

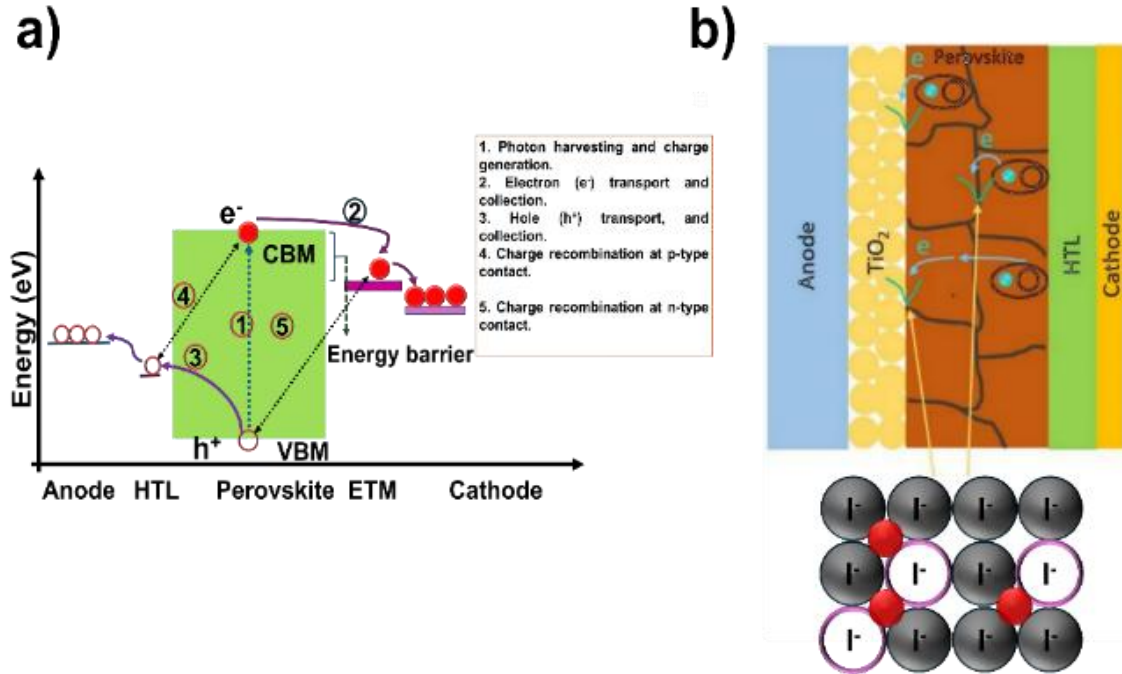


Figure 3. a) The mechanism of radiative recombination of photo-induced charge carriers[86], and b) Defect recombination mechanism at ETM/perovskite interface[90].

Non-emissive recombination in PSC primarily occurs due to mismatched energy levels or DSs leading to thermal potential loss and significantly reducing the open-circuit voltage (V_{oc}) and fill factor (FF) [91]. This misalignment causes thermal potential loss and primarily reduces the V_{oc} and FF of the devices. Therefore, the suitable energy levels of the ETM as well as HOMO/LUMO, are critical parameters for device performance[92]. A high-quality ETM with appropriate energy levels facilitates efficient electron transport and hole blocking, enhancing overall efficiency.

The collection of charge carriers by HTLs or ETMs occurs via the built-in electric field (E_{bi}). The energy offsets (ΔE) between the LUMO level of ETM and the HOMO level of HTL are critical for minimizing non-emissive recombination. Lower values of ΔE_1 of the valence band and ΔE_2 of the CB decrease recombination rates, while higher values increase them. Optimal band offsets, ideally below 0.2 eV, enhance charge transport and reduce interface recombination. Therefore, the selection of the conduction or valence band of the HTL /ETM, or the LUMO/HOMO for molecular CTLs, is critical to ensure selective charge extraction. This is achieved by establishing an energetic barrier that effectively facilitates the specific extraction of electrons or holes, thereby boosting the efficiency and performance of the device.

2.2.2 Tuning charge dynamics at the interface through chemical engineering:

Interface layers (ILs) extend their influence beyond optimizing ELA. They possess the valuable capability to passivate defects and traps residing at the active layer surface or interface[57]. Passivation involves applying a protective layer, typically a material that chemically interacts with the base substrate, to form a micro-coating that provides protection. The transition from an active to a passive state is achieved through the creation of this passivation layer. In PSCs, passivation typically arises through two mechanisms: chemical passivation and physical passivation[93, 94].

Chemical passivation focuses on minimizing DSs to improve charge transfer across interfaces, while physical passivation involves shielding specific functional coatings from environmental exposure to prevent cell degradation. These passivation techniques are essential for optimizing PSCs, resulting in improved PCE and overall performance.

The interface between the CTL and the perovskite may exhibit weak adhesion because of inhomogeneities in composition and the presence of strain within the light-harvesting layer. Such inhomogeneities could potentially result in a diminished homojunction of the perovskite next to the CTLs. The potential for a WF discrepancy at the perovskite homojunction as, characterized by weak adhesion, suggests that the interface may adversely affect stability. Thus, it is imperative to regulate the WF to improve overall stability, (Figure 2d). Consequently, there is a need to explore strategies for assessing the WF of the weak homojunction within the light-harvesting layer that is situated near the CTL. The n-i-p configuration featuring a SnO₂ CTL detachment of the perovskite layer from the SnO₂-coated fluorine-doped tin oxide (FTO) substrate may serve as an effective approach to assess the WF of the weakly adhering homojunction. The light-harvesting layer was partially removed from the SnO₂-coated FTO substrate; however, a residual thin layer of perovskite remained attached to the SnO₂ surface. The bottom surface of the perovskite film and the top surface of the SnO₂ film were identified as "surface A" and "surface B," respectively. The WF values for surface A and surface B were measured at 4.23 eV and 3.88 eV, respectively, (Figure 2e), as determined by a Kelvin probe force microscope (KPFM). This variation in WF indicates the formation of a homojunction.

3.0 Recent progress in ETMs.

In PSCs, the ETM is situated between the metal electrode and the light-harvesting layer[95]. This layer plays a crucial role in modifying the interface by generating an interfacial dipole, which subsequently alters the vacuum level. Such modifications facilitate electron extraction by reducing the energy barrier at the interface. By establishing an efficient connection between the metal electrode and the photovoltaic active layer, the ETM effectively minimizes energy losses and recombination during charge extraction, thus enhancing the PCE of PSC[32]. A promising ETM is characterized by well-aligned energy levels with the light-harvesting layer. Specifically, having its LUMO/HOMO positioned elevated than those of the perovskite layer. Furthermore, the ETM should demonstrate high transmittance in the UV-Vis spectrum to ensure that photons can easily penetrate the perovskite absorbed by it. The evaluation of transmittance, absorption spectra, mobility, and conductivity are used to assess the optical and electronic properties.

3.1 Metal Oxides (MOs) based ETMs.

In recent years, the development of Metal oxides (MOs) has been preferred as ETMs due to their facile fabrication process[96], high intrinsic stability, tunable optical and electronic properties[97], low-temperature or no post-treatment requirements[70], low cost, and additional passivation function. These benefits enhance their application in high-performance inverted PSCs.

3.1.1 Titanium Oxide (TiO₂)

TiO₂ has garnered significant attention as an ETM due to its advantageous positions (HOMO/LUMO) that facilitate the extraction and injection of charge carriers. Its high electron mobility, appropriate energy levels, and robust chemical stability further contribute to its suitability

as an ETM [98-100]. Khan et al. achieved 22.10 % PCE using TiO_2 as ETM with CsSnI_2Br based PSC using numerical calculations [101]. However, TiO_2 faces several challenges, particularly its high processing temperatures and photocatalytic activity, which can degrade device stability[102, 103]. Recent studies have attempted to overcome these limitations through doping and nanoengineering. Doping TiO_2 with elements such as nitrogen and fluorine has enhanced its electrical conductivity and light absorption properties, while Nanoengineering approaches like creating nanorods and nanotubes have improved electron transport and reduced recombination losses[104]. Despite these advancements, there are still some issues with TiO_2 as an ETM material, such as UV degradation. Upon exposure to light, TiO_2 undergoes bandgap excitation, leading to the generation of electron-hole pairs[105, 106]. The photoexcited electrons can migrate to the surface of the TiO_2 , where they interact with the adsorbed oxygen molecules[107]. This phenomenon can induce the desorption of oxygen species from the surface, thereby destabilizing the charge transfer complex. The consequent depletion of surface-adsorbed oxygen species, crucial for passivating surface defects on TiO_2 , results in the proliferation of recombination centers.[102]. Consequently, this leads to a degradation of photocurrent and overall device performance. Additionally, the high processing temperatures required for TiO_2 , exceeding 450°C , pose a significant challenge, particularly for applications that involve flexible PSC devices[79].

3.1.2 Zinc oxide (ZnO)

The requisite high processing temperatures for TiO_2 constrain its utility as an ETM for PSCs. Consequently, ZnO 's suitability for low-temperature processing renders it an auspicious candidate for the ETM in flexible PSCs, additionally providing a cost-effective alternative to the high-temperature sintering demanded by TiO_2 [108]. ZnO has demonstrated superiority over TiO_2 as an

ETM, attributable to its elevated electron mobility (Table 2) that enables rapid electron transport. Among the various deposition techniques for ZnO ETLs in planar PSCs, solution-based methods such as the sol-gel process have been extensively investigated. In 2014, Lee and co-workers reported the fabrication of planar PSCs employing sol-gel-derived ZnO ETLs, achieving a PCE of 8.37% [109].

Table 2. Photovoltaic Features of TiO₂ , SnO₂, and ZnO [112-121].

	TiO₂	ZnO	SnO₂
Energy band gap (eV)	3.0-3.2	3.2 - 3.3	3.50 – 4.0
Electron mobility (cm ² ·V ⁻¹ ·s ⁻¹)	20	2.05 × 10 ²	10 ⁻⁸ -10 ²
Efficiency% (η)	20-25	19-21.90	23-26
Surface work function (eV)	4.5-5.0	4.45 – 5.3	4.71 – 5.3
Electron diffusion coefficient (cm ² s ⁻¹)	0.5-10 ⁻⁸	5.2 - 1.7×10 ⁻⁴	6.22×10 ⁻⁶

Recently, there has been a significant surge in interest in developing low-temperature processable PSCs, driven by the escalating demand for this cutting-edge technology in the photovoltaic industry. ZnO is one of the most promising candidates and is extensively studied due to its superior optoelectronic properties compared to TiO₂, providing numerous advantages, especially in the realm of charge dynamics. ZnO can be processed at much lower temperatures compared to TiO₂, making it compatible with flexible and organic substrates. ZnO demonstrates superior electron mobility, enhancing charge transport efficiency and minimizing recombination losses. This higher mobility is partly due to ZnO intrinsic properties and its ability to form various nanostructures, such as nanorods, nanowires, and nanoparticles, which enhance the surface area and improve electron extraction. Recent advancements in ZnO ETMs include doping with

elements like aluminum and gallium to further increase conductivity and reduce defects and developing composite materials that combine ZnO with other oxides or organic molecules to improve performance and stability. Surface passivation techniques have also been employed to mitigate surface defects and recombination sites, leading to improved device stability and efficiency.

Despite the potential to resolve the high-temperature processing limitations, ZnO-based PSCs remain vulnerable to substantial long-term stability problems, primarily due to UV degradation[122]. The stronger UV catalytic activity of ZnO leads to severe degradation issues, than TiO₂. Surface hydroxyl groups and residual chemicals on the solution-processed ZnO surface induce photochemical reactions under UV exposure, accelerating the decomposition of the light-harvesting layer. This degradation mechanism critically undermines the stability and efficiency of ZnO-based PSCs, highlighting the urgent need for strategies to enhance their UV resistance. The interaction between ZnO and metal halide perovskites results in the chemical instability of ZnO, which triggers a swift deterioration of the perovskite layer[123]. This instability hinders the potential use of ZnO as an n-type charge extraction layer in high-performance PSCs, despite its superior optoelectronic properties compared to other MOs like SnO₂ and TiO₂.

3.1.3 Tin oxide (SnO₂)

The predominant challenge associated with MOs, such as TiO₂ and ZnO, is their interaction with ultraviolet (UV) light. Under UV irradiation, these materials function as photocatalysts, thereby enhancing the degradation process of perovskite materials. This degradation process is initiated when UV light excites electrons within TiO₂, leading to the creation of deep-level defects and augmented interface carrier recombination. These phenomena collectively result in a substantial

diminution of PSC performance. Typically, SnO₂ is recognized for its excellent UV light absorbance due to its wide band gap, which makes it an effective photocatalyst under UV radiation[124, 125]. SnO₂ being chemically inert with negligible catalytic performance, and its larger BG compared to TiO₂ makes it less susceptible to these issues. SnO₂ UV resistance and lower photocatalytic activity contribute to its ability to maintain device stability and lifespan under UV exposure, providing a more stable alternative as an ETM in PSCs. Additionally, SnO₂ boosts significantly higher electron mobility, up to $240 \times 10^{-4} \text{ cm}^2 \cdot \text{V}^{-1} \cdot \text{s}^{-1}$, compared to TiO₂ ($10^{-4} \text{ cm}^2 \cdot \text{V}^{-1} \cdot \text{s}^{-1}$) (Table 1)[126]. This higher electron mobility facilitates more efficient electron collection and transport, directly contributing to improved device performance. Furthermore, the reduced hygroscopic nature and enhanced resistance to acidic conditions of SnO₂ contribute to its longevity, resulting in solar cells with extended operational lifespans. The fabrication process of SnO₂ also presents significant advantages. SnO₂ can be synthesized at low temperatures (<180 °C), in contrast to the high-temperature processes often required for TiO₂. The nanocrystalline SnO₂, processed through low-temperature solution methods, can effectively function as a viable substitute for TiO₂ as an ETM. A wide range of electron mobility values for SnO₂ (from 10^{-8} to $10^2 \text{ cm}^2 \cdot \text{V}^{-1} \cdot \text{s}^{-1}$) has been reported (Table 2), which can be primarily attributed to variations in synthesis methods, crystallinity, and defect concentrations. Factors such as oxygen vacancy density, grain boundary scattering, and surface roughness critically influence charge transport. Films prepared via low-temperature or solution-based processes often exhibit poor crystallinity and high defect densities, leading to reduced mobility. In contrast, high-temperature or vacuum-based techniques generally produce well-ordered structures with significantly improved mobility [127]. Furthermore, SnO₂ offers excellent band alignment with Light-harvesting layers, which is crucial for efficient electron transfer and minimizing energy losses [128]. This favorable CB alignment

helps form high-quality p-n heterojunctions, reducing charge recombination and thereby improving the V_{oc} and FF of the PSCs. The ability of SnO_2 to serve both as a compact layer and a mesoporous layer adds to its versatility, allowing for more flexible design and optimization of PSC architecture. This versatility is instrumental in achieving higher efficiencies and developing more robust and scalable solar cell designs. However, SnO_2 as an ETM in PSCs faces challenges, including the need for dense, pinhole-free films, as pinholes can reduce efficiency. Low-temperature annealing can cause defects, increasing charge carrier recombination and reducing device performance. Additionally, SnO_2 films often require surface treatments, like UV-ozone, to remove residues and improve wettability, adding complexity to the manufacturing process. The intricate surface characteristics inherent to TMOs, notably including oxygen vacancies, ionic residues, and suspended bonds, introduce supplementary non-emissive recombination sites. Consequently, these phenomena exert adverse effects on the crystallization and interfacial contact of the Light-harvesting layer, thereby impeding device performance and stability. Moreover, the disparate carrier mobility and limited conductivity exhibited by ETMs and HTLs contribute to the accumulation of carriers at interfaces and consequent resistance losses. These challenges exacerbate hysteresis effects and promote charge recombination within the device structure [129].

3.2 Organic ETMs

The limitations of metal oxide-based ETMs, particularly their high processing temperatures and incompatibility with flexible substrates, have driven significant interest in organic alternatives. Organic ETMs offer distinct advantages, including solution processability, tunable electronic properties, and compatibility with roll-to-roll (R2R) fabrication, making them indispensable for scalable and flexible perovskite photovoltaics[130]. Among these, fullerene derivatives (e.g., C_{60} ,

PCBM) have emerged as leading candidates due to their exceptional electron affinity and ability to passivate interfacial defects, enabling PCEs exceeding 22% in optimized devices[131, 132].

Despite their advantages in processing versatility and interfacial engineering, organic ETMs face intrinsic limitations that constrain their widespread adoption in PSCs[133], such as Lower electron mobility ($<10^{-2} \text{ cm}^2 \cdot \text{V}^{-1} \cdot \text{s}^{-1}$) compared to inorganic ETMs (e.g., SnO_2 , TiO_2), leading to resistive losses in thick-film devices[134]. Furthermore, interfacial energy disorder at perovskite/ETM junctions exacerbating non-radiative recombination losses, while the thermodynamic instability of carbon-based molecular frameworks under operational stressors (photo-oxidation, thermal degradation) poses fundamental challenges for long-term device viability[32]. These material-level constraints underscore the need for innovative molecular design strategies that reconcile electronic performance with environmental robustness to unlock the full potential of organic ETMs in commercial PSC architectures.

4. Exploring the charge dynamics of Fullerenes and Fullerene Derivatives in PSCs.

Fullerenes and their derivatives are pivotal in PSCs due to their high electron affinity, tunable energy levels, and defect passivation capabilities. This section examines how pristine and functionalized fullerenes optimize photocarrier dynamics, charge generation, separation, transport, and recombination, and highlights recent spectroscopic insights into their molecular-level contributions.

4.1 Pristine Fullerene

While n-type metal oxides have traditionally dominated as ETMs in conventional PSCs, their practical implementation faces significant limitations. These include suboptimal film quality, oxygen vacancy-induced defect states, inherent chemical instability, and pronounced hysteresis effects, all of which collectively constrain device performance metrics. In contrast, Pristine fullerenes (C_{60} and C_{70}), serve as effective ETMs due to their LUMO levels ($\sim 3.7\text{--}4.0$ eV), which align well with perovskite conduction bands[30]. Their icosahedral structure enables efficient electron extraction, reducing recombination losses. For example, C_{60} -based PSCs achieve PCEs of 20–23%[135]. However, their hydrophobicity and tendency to aggregate limit film uniformity, increasing trap states and reducing carrier diffusion lengths (<100 nm)[136].

4.2 Fullerene derivatives

The optimization of photocarrier dynamics in perovskite solar cells necessitates the strategic functionalization of fullerene derivatives (Figure 4a)[7], as the implementation of pristine fullerenes as ETM presents significant limitations. Poor solubility in common organic solvents (chlorobenzene, chloroform), restricting processing window. Non-uniform films with incomplete surface coverage ($<80\%$), leading to inconsistent charge transport pathways. This morphological imperfection creates inconsistent charge transport pathways and compromises interfacial contact with the perovskite layer, ultimately manifesting as increased series resistance exceeding $10\ \Omega\cdot\text{cm}^2$ and elevated trap-assisted recombination with carrier lifetimes shorter than 20 ns[9, 129]. Functionalized fullerenes, such as PCBM, are limited by issues including photochemical instability, high cost, and restricted tunability [31]. In contrast, non-fullerene ETMs offer enhanced structural diversity, tunable electronic properties, and improved film morphology [137]. For example, perylene diimides (PDIs) and naphthalene diimides (NDIs) have demonstrated comparable or even

superior device performance with enhanced long-term stability, achieving PCEs of up to ~20.5%. Moreover, polymer-based ETMs such as P(NDI2DT-TTCN) and PFN-2TNDI exhibit excellent processability, thermal stability, and competitive efficiencies ranging from ~17% to 20.8%. Additionally, oxygen-doped graphitic carbon nitride has been shown to enhance ETM performance in PSCs by passivating interfacial trap states and improving energy level alignment. This results in reduced charge recombination, improved charge extraction, and PCEs exceeding 21%, along with enhanced device stability. Nonetheless, challenges persist in achieving consistently high charge mobility and scalable fabrication [31].

This review systematically examines key classes of fullerene derivatives (Figure 4b), focusing on their role in optimizing charge dynamics in PSCs. Notably, functionalized fullerenes such as PCBM and 5F-PCBP (Figure 4c) effectively passivate iodine vacancies at perovskite interfaces, thereby enhancing charge extraction efficiency. Further modifications, including hydrophilic variants (-OH, -COOH, -NH₂), improve both solution processability and interfacial charge extraction, addressing critical limitations of pristine fullerenes[7]. Lewis acidic derivatives effectively modify cathode work functions for better energy alignment. Halogenated fullerenes demonstrate increased electron affinity, benefiting open-circuit voltage[138]. Oligoethylene glycol and crown ether modifications significantly broaden solvent compatibility. Pyridine/thiophene-functionalized derivatives excel in defect passivation through Pb²⁺ coordination (Figure 4d). Cross-linked versions create robust, thermally stable charge transport networks. Notably, ICBA and its analogues with elevated LUMO levels have proven particularly effective for achieving higher photovoltages[139]. Each derivative class offers distinct advantages for addressing specific challenges in charge carrier management, as will be explored in subsequent sections. This strategic

functionalization enables precise tuning of electronic properties, interfacial interactions, and morphological stability in PSC architectures.

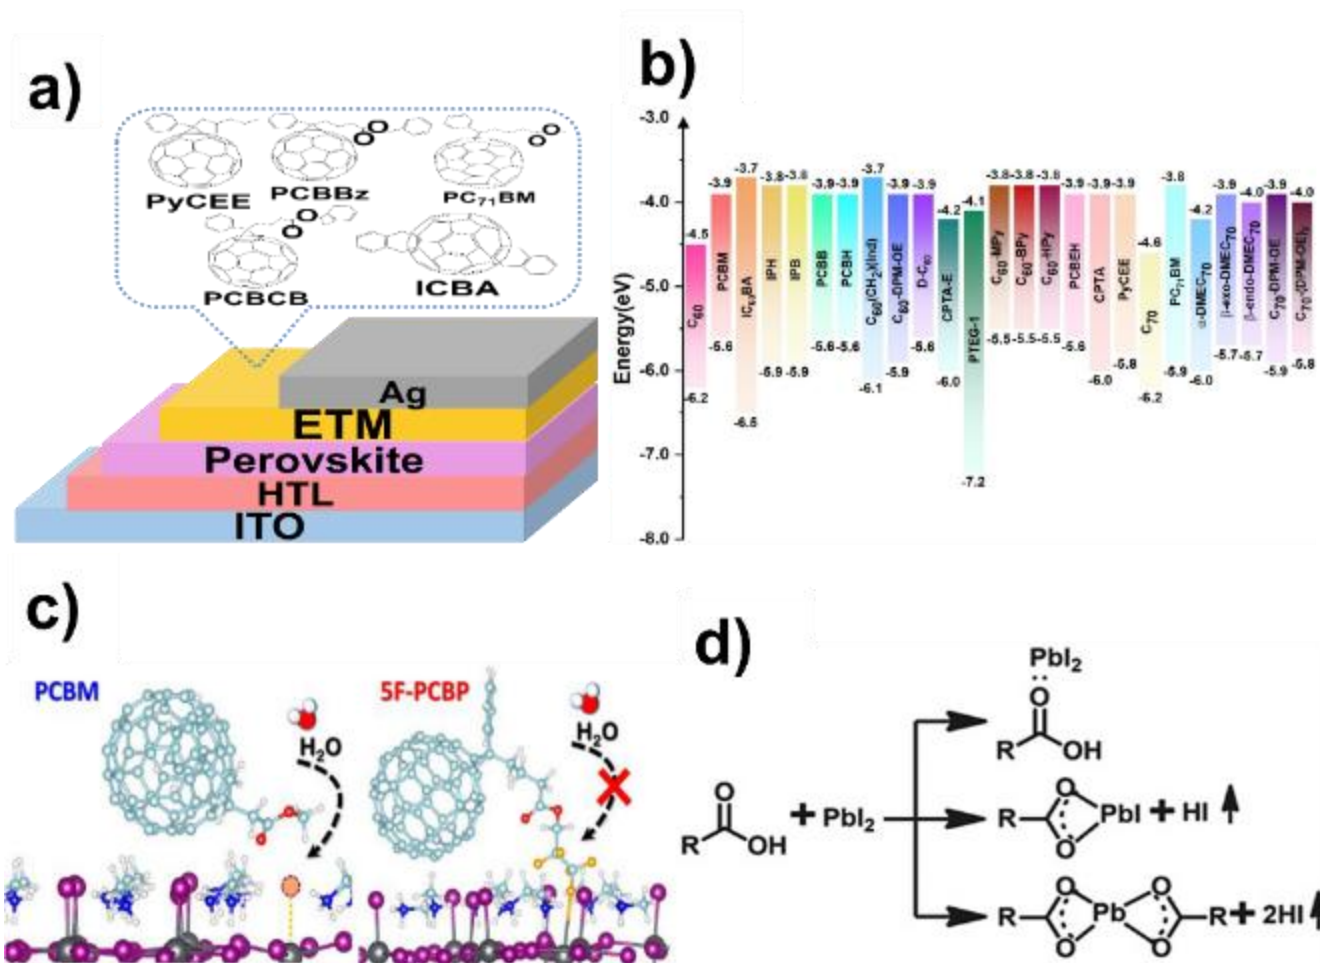


Figure 4. a) The structural design of fullerene derivatives and illustration of the planar PSC, b) Energy level diagram of various functionalized fullerenes in PSCs[30], c) The interface between the perovskite/PCBM and perovskite/5F-PCBP layers reveals the presence of iodine vacancies on the perovskite surface[140], and d) Proposed pathways for the formation of CPTA: PbI₂ complexes[141].

4.3 Hydrophilic Fullerene

The intrinsic hydrophobicity of pristine fullerenes poses substantial challenges for their effective integration into perovskite solar cell architectures, particularly in solution-processed fabrication methods[136]. This limitation stems from strong π - π stacking interactions that promote aggregation and poor interfacial compatibility with polar components in the device stack. To address these constraints, researchers have developed three principal strategies to enhance hydrophilicity and processability. The first approach involves the formation of stable colloidal aggregates through carefully controlled solvent exchange processes, where extended sonication aids in achieving uniform dispersion. A second pathway utilizes non-covalent modification techniques that leverage hydrogen bonding networks, π - π stacking interactions, or electrostatic stabilization to improve aqueous compatibility without altering the core fullerene structure. Notably, covalent functionalization with hydrophilic moieties (-OH, -COOH, -NH₂ groups) has emerged as the most versatile solution, (Figure 5a). These chemical modifications not only dramatically improve solubility in polar media but also introduce beneficial interfacial properties that enhance charge extraction while maintaining the essential electronic characteristics of the fullerene core.

The C₆₀'s icosahedral symmetry limits functionalization to specific carbon atoms, affecting the degree of modification. Wang et al. demonstrated this principle by developing 5F-PCBP, a fluorinated PCBM derivative, which achieved a remarkable PCE of 21.27% in triple-cation PSCs, (Figure 4)[142]. The fluorinated ETM exhibited exceptional stability, with encapsulated devices showing a projected T₈₀ lifetime exceeding 92,700 hours (~10 years) under operational conditions. This performance enhancement stems from the synergistic effects of fluorination: increased

surface hydrophobicity, suppression of iodine vacancies, and stabilization of organic cations at the perovskite interface.

Alternative modification strategies have explored polar functional groups to optimize interfacial properties. Chang and colleagues investigated CPTA-E (Figure 5b), a fulleropyrrolidine derivative featuring three carboxylic ester groups, as a PCBM alternative in p-i-n PSCs (Figure 5(c,d))[33]. While CPTA-E shows reduced solubility in chlorobenzene compared to PCBM, solvent blending with chloroform enabled effective processing. More critically, the carbonyl groups in CPTA-E strongly coordinate with undercoordinated Pb^{2+} ions at the perovskite surface, forming a uniform passivation layer that reduces interfacial recombination. This molecular design yielded devices with 17.44% PCE and minimal hysteresis, outperforming PCBM-based control devices (15.09% PCE with pronounced hysteresis). Cross-sectional SEM analysis (Figure 5e) confirmed the improved morphology and interfacial integrity achieved with CPTA-E.

These case studies illustrate how targeted functionalization of fullerenes can simultaneously address multiple challenges in PSCs, enhancing solubility, improving interfacial charge extraction, and boosting device stability through carefully engineered molecular interactions at the perovskite/ETM interface, (Figure 5f).

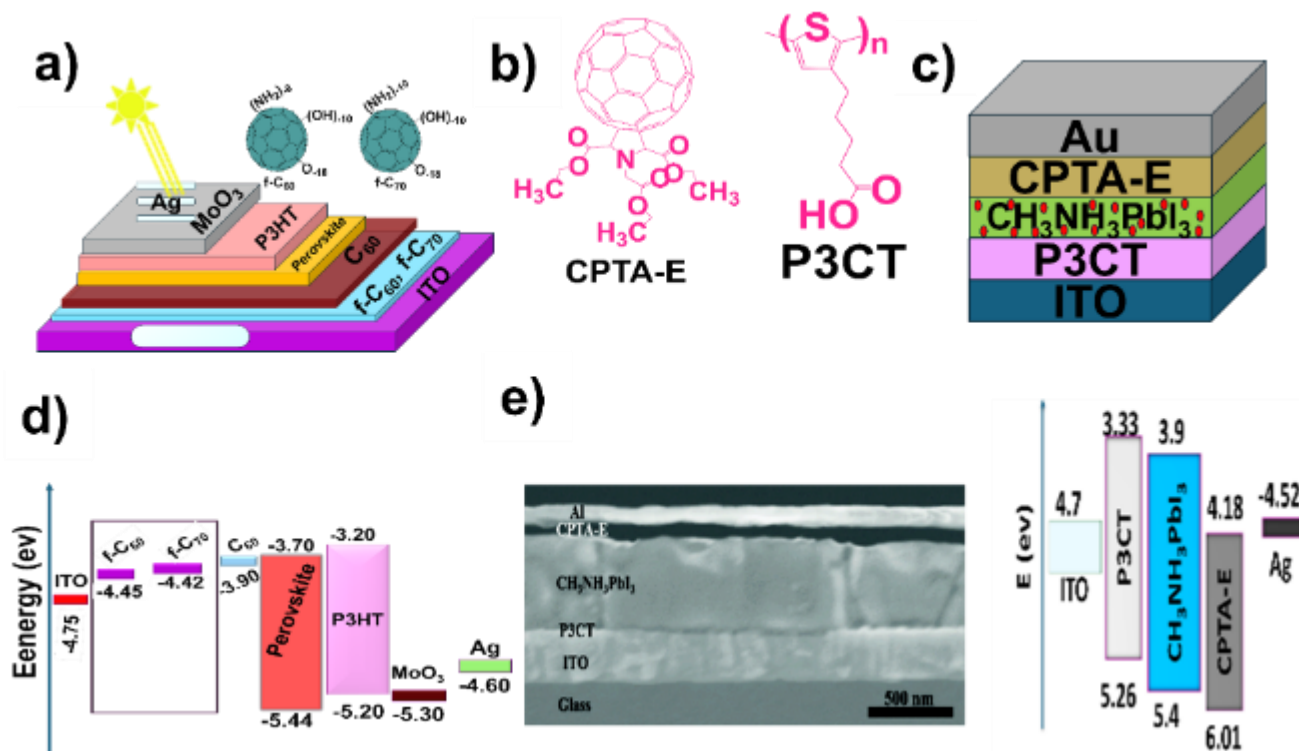


Figure 5. a) Schematic diagram of hydrophilic fullerene[143], b) The chemical configurations of CPTA-E and P3CT,c) A schematic depiction of the p-i-n structured PSC device employing CPTA-E as the ETM along with its corresponding d) energy level diagram, and e) SEM image showing a cross-section of the device and energy level diagram for each layer is shown correspondingly [144].

4.4 PCBM-Based Fullerene Derivatives.

The ELA between MAPbI₃ perovskites and fullerene derivatives presents both opportunities and challenges for charge carrier management. While the 0.7 eV ΔE between the MAPbI₃ valence band and C₆₀'s HOMO level provides adequate hole-blocking capability, this configuration is not optimal for maximizing device efficiency. This ΔE creates conditions where photogenerated holes may transfer to adjacent C₆₀ molecules, leading to interfacial recombination losses. PCBM

exacerbates this issue further, with a reduced 0.4 eV valence band offset between the perovskite valence band and the HOMO level (compared to C₆₀) further compromises hole-blocking efficiency. This limitation necessitates the implementation of additional interfacial layers to optimize charge extraction dynamics[145].

A more fundamental challenge arises from defect states (DSs) associated with perovskite crystallinity, particularly at grain boundaries (GBs) and CTL interfaces. These structural imperfections act as trapping centers for charge carriers before they reach the electrodes. Fullerenes mitigate these defects through two primary passivation mechanisms: (1) physical passivation by filling GB voids via large molecular size, and (2) chemical passivation [through coordinating undercoordinated Pb²⁺/I⁻ ions, as well as electronic passivation by delocalized π -electrons quench trap states. However, PCBM's tendency to form large aggregates during deposition reduces interfacial contact area, and its photodimerization under illumination significantly degrades charge transport properties[146]. Recent advances in evaporable fullerene derivatives, such as the fullerene indanones (FIDOs) developed by Shui et al., have addressed these limitations. FIDO-based devices achieved a remarkable 22.11% PCE compared to 18.2% for conventional C₆₀ devices, though long-term stability remains a concern[147].

Edison Castro and colleagues systematically investigated the structure-property relationships of PCBEH (Figure 6a), a PCBM analogue functionalized with branched alkyl chains, demonstrating significant improvements in both device performance and stability[7]. Their study, employing dynamic light scattering (DLS) and solution-state NMR, confirmed PCBEH's superior chlorobenzene solubility (~52 mg/mL) vs. PCBM (~35 mg/mL), enabling the formation of exceptionally uniform thin films with enhanced interfacial properties. This improved morphology directly correlated with more effective defect passivation and optimized electron extraction

dynamics, ultimately yielding champion devices with power conversion efficiencies reaching 16.26% - a notable improvement over standard PCBM-based architectures[142].

The branched alkyl functionality of PCBEH contributed to two key advantages: first, the enhanced hydrophobicity (contact angle of 97° versus PCBM's 81°) provided superior moisture resistance, and second, the optimized molecular packing reduced interfacial trap states[148].

Atomic force microscopy characterization (Figure 6b) provided quantitative insights into the morphological improvements, showing that PCBEH deposition on perovskite substrates reduced the root-mean-square surface roughness from 54 nm (bare perovskite) to 13.7 nm, outperforming PCBM's smoothing effect to 19.3 nm (Figure 6c). This dramatic reduction in surface roughness reflects PCBEH's ability to more effectively template the perovskite interface, minimizing contact imperfections that typically promote non-radiative recombination. The combination of enhanced solution processability, improved interfacial morphology, and intrinsic hydrophobicity positions alkyl-functionalized fullerene derivatives like PCBEH as promising candidates for developing high-performance as well as environmentally stable perovskite photovoltaics. These findings underscore the critical importance of side-chain engineering in tailoring fullerene derivatives for specific interfacial challenges in PSC architectures[149].

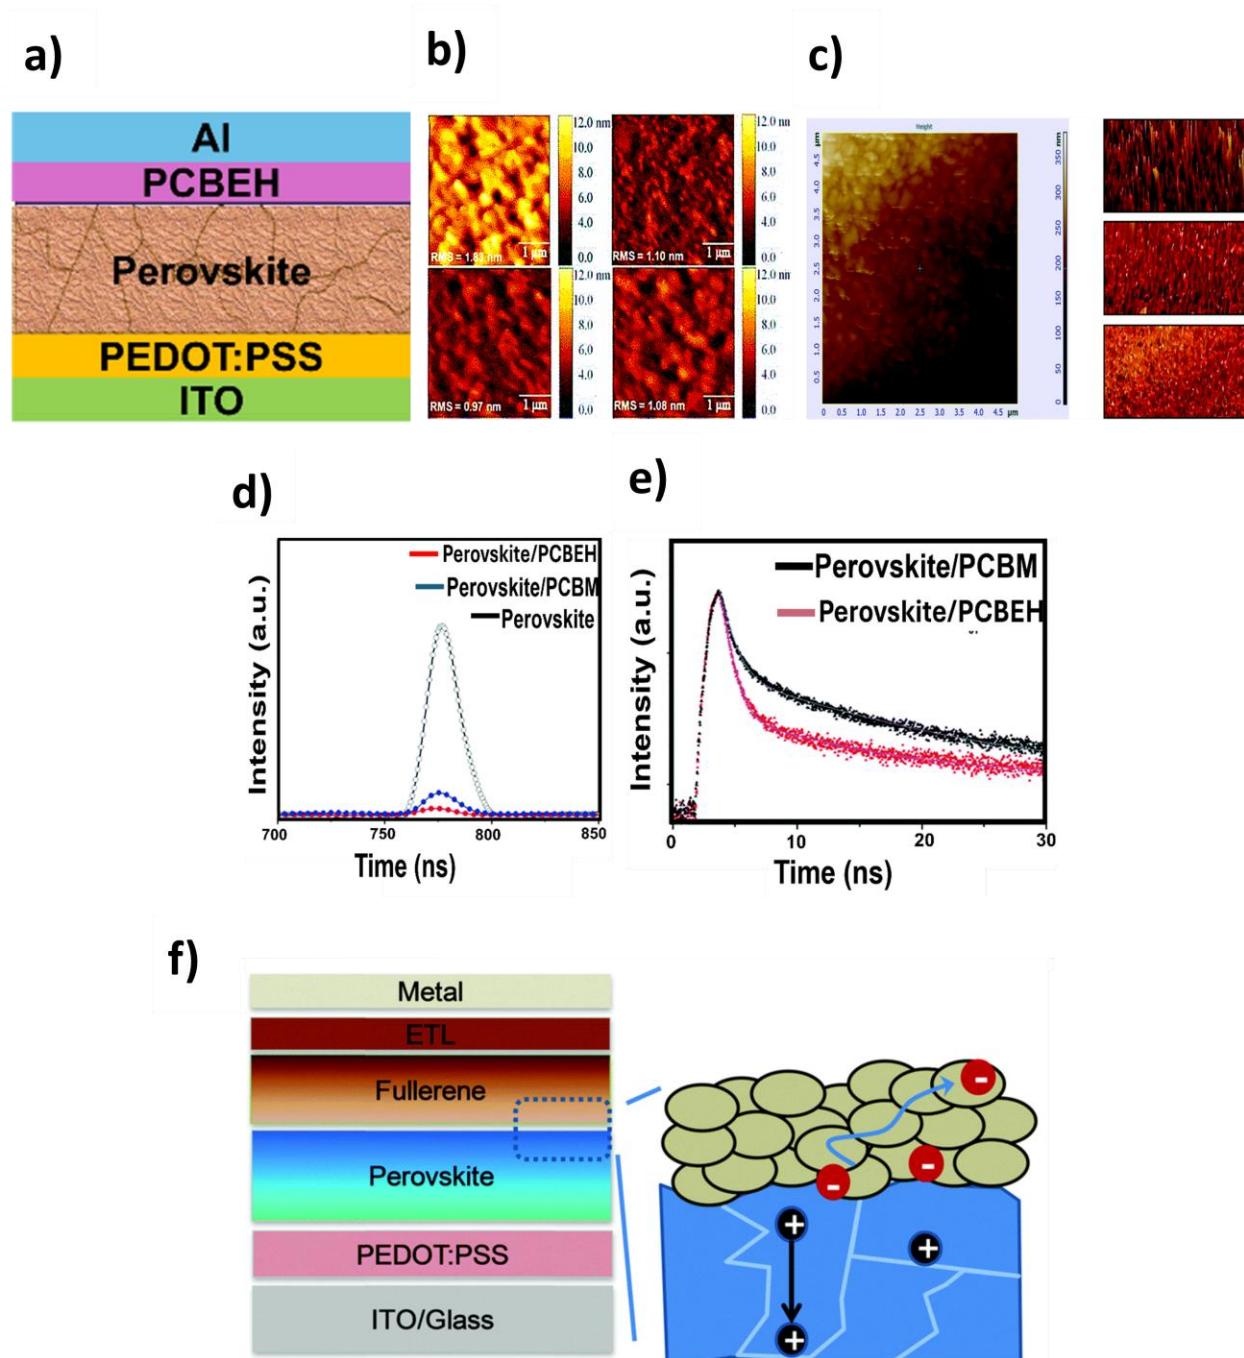


Figure 6. a) An illustration of PCBEH-based PSC[150]. b) AFM images for the perovskite/PCBM: C₆₀ configuration, highlighting various volume ratios of PCBM: C₆₀, c) the PL and TRPL decay transient spectra of the FTO/perovskite/PCBM (or PCBEH)[151], (d) A schematic representation of the layer configuration of fullerene-based PSCs, with and without the application of PCBB-3N-

3I, and e) Chemical structures of FDs and their charge transfer mechanism on perovskite films[144].

4.5 [6,6]-phenyl-C61-butyric acid benzyl ester (PCBB)

To overcome PCBM's photoinduced aggregation, Wei et al developed PCBB, a structural analogue where the terminal methyl group is replaced with a benzyl moiety[33]. This strategic modification significantly enhances molecular stability and retain >80% initial PCE after 600 hours at maximum power point ,achieves 19.84% PCE (Table 3), a marked improvement over conventional PCBM-based systems. This enhanced performance stems from two key molecular interactions: (1) strengthened π - π stacking between C₆₀ cages that maintains electron delocalization, and (2) CH- π bonding between benzyl groups that provides steric stabilization. Together, these interactions effectively suppress fullerene aggregation - a critical advancement over conventional PCBM systems. Recent studies by Zhang et al. have further confirmed that such aromatic substitutions in fullerene derivatives reduce trap state formation at perovskite interfaces (Figure 7a), explaining the observed enhancement in both efficiency and operational stability[152]. This molecular design approach (Figure 7b) offers a promising pathway to overcome one of PCBM's most persistent limitations in PSC applications.

Table 3. presents the photovoltaic characteristics of devices incorporating various functional additives based on fullerenes[104, 107, 112, 140, 142, 144, 148, 153-163].

Compounds	LUMO/eV	μ (cm².V⁻¹.s⁻¹)	FF/%	PCE%
PCBM	-3.70	-	58.37	21-23
PCBB	-3.90	3.09×10^{-4}	80.39	19.84
PCBA	-4.2	-	72	17.76
CPTA	-3.9	5.4×10^{-3}	75.61	18.39
Sol-gel C ₆₀	-3.85	3.8×10^{-4}	73	17.9
PCBCB	-3.8	5.9×10^{-3}	73	17.9
MPMIC ₆₀	-4.1	-	64	13.8
PCBC	-	-	81	15.71
C ₆₀ -MPy	-3.80	1.97×10^{-3}	78.4	16.1
CPTA	-3.9	5.4×10^{-3}	75.61	18.39
ICBA	-3.74	3×10^{-3}	79	23.8
ICTA	-3.36	-	74.2	18.04
ICMA	-3.85	-	64.7	13.9
CPTA-E	-4.18	3.8×10^{-4}	80	17.44
C ₆₀ -MPy	-3.80	1.97×10^{-3}	78.4	16.1
C ₆₀ -HPy	-3.83	1.04×10^{-3}	70.8	14.4
C ₆₀ -BPy	-3.81	3.51×10^{-3}	74.2	18.22
PCP	-3.81	2.64×10^{-3}	78	19.32
PyCEE	-3.94	5.76	75.83	18.27
PCBBz	-3.80	3.70×10^{-4}	69	16.57
PCBH	-3.90	-	79	13.75

4.6 Lewis Base Functionalized Fullerene Derivatives.

Functionalizing fullerenes with Lewis base groups (amines, oligoethers, crown ethers) improves their performance as ETMs by simultaneously enhancing polarity (enabling better processing), defect passivation (via Pb^{2+} coordination), and ELA at perovskite interfaces[164]. These modifications strengthen interactions with ionic species in perovskites, reducing recombination while maintaining charge transport efficiency, a key advancement beyond conventional ester/alkyl modifications.

4.6.1 Amino-functionalized fullerene derivatives

Amino groups, including $-\text{NH}_2$ and $-\text{N}^+(\text{CH}_3)_3\text{I}^-$, serve as effective Lewis bases for fullerene functionalization, creating dipole-induced fields that enhance charge collection through dipole-induced built-in electric fields[140]. These modifications simultaneously passivate defects and modify interfacial energy bands. Xiang et al. demonstrated the dual functionality of C_{60}NH_2 by employing it as a modifier for the TiO_2 ETM in planar n-i-p PSCs, achieving a PCE of 18.34%. The enhanced performance was attributed to reduced hysteresis resulting from improved electronic coupling at the perovskite/ TiO_2 interface and lattice stabilization[165].

Further advancements emerged from Li et al.'s PCBB-S-N (Figure 10d), combining thiophene and amino groups into an interlayer that reached 21.08% PCE. The thiophene moiety coordinated with Pb^{2+} ions while the amino group formed hydrogen bonds, producing dense PCBM films and optimized energy band alignment. Zhang et al. extended this approach with PCBB-3N-3I, where Coulombic interactions with charged defects yielded 21.1% PCE and enhanced stability through defect neutralization and dipole layer formation [166]. For inverted architectures,

PCBDMAM interlayer boosted PCE from 14.21% to 18.10% by reducing the Ag cathode work function and minimizing interfacial barriers between PCBM and electrodes[167].

4.5.2 Oligoether and crown-ether functionalized fullerene:

The exploration of polar Lewis bases beyond amino groups has opened new avenues for fullerene-based ETMs, with crown ether (CE) and oligoether (OE) functionalizations demonstrating particular promise. This development builds on earlier work with amino groups, extending the toolkit for interfacial engineering in PSCs. Jen et al. pioneered this approach by developing bis- C_{60} as a cathode buffer layer (CBL), where its unique structure improved ELA between PCBM and Ag electrodes, achieving 11.8% PCE [168].

This advanced designs inspired subsequent innovations, such as Li et al.'s bis-FIMG and bis-FITG CBLs, which reached ~19% PCE by combining the conductivity advantages of fullerene derivatives with improved work function modulation[169].

The relationship between molecular structure and device performance becomes particularly evident in Cao et al.'s systematic study of OE-functionalized fullerenes. Their optimized C_{70} -DPM-OE derivative, featuring electron-rich OE chains, not only enhanced interfacial charge mobility but also effectively passivated defects, yielding 16% PCE[170]. This success highlights how tailored functional groups can address multiple device challenges simultaneously. Further insights into molecular interactions emerged from comparative studies of different Lewis base functionalities. MCM (OE-functionalized) and PCP (pyridine-functionalized) derivatives (Figure 7d) revealed a crucial structure-property relationship: while the stronger N- Pb^{2+} coordination in PCP improved interfacial contact, it also introduced energetic misalignment that exacerbated hysteresis. The crown-ether approach developed by Liu et al. with PCBC demonstrated how molecular engineering can improve interfacial physics. By serving as an

effective CBL between PCBM and aluminum electrodes, PCBC enhanced Ohmic contact and electron extraction, achieving 15.08% PCE. The subsequent development of PCBC/LiF bilayers further improved performance (15.53% PCE), illustrating the cumulative benefits of layered interfacial engineering.

Parallel developments in PEG-functionalized fullerenes addressed the critical challenge of device stability. Delgado et al. showed that increasing PEG moieties enhanced moisture resistance, while Wu et al. and Hu et al. demonstrated how PEG-capped derivatives could simultaneously improve crystallinity, reduce defects, and enhance charge transfer, with PCEs consistently around 17.7% [171, 172]. These studies collectively established PEG-functionalization as a versatile strategy for stability enhancement.

The critical role of chemical bonding mechanisms was conclusively demonstrated by Huang et al.'s comparison of CPTA and PCBM on SnO₂ surfaces (Figure 7(c,e)). The strong chemical bonding of CPTA's carboxyl groups created beneficial interfacial dipoles (Figure 7f), reducing recombination and achieving 19% PCE - significantly outperforming PCBM's physisorption approach (17.9% PCE) and unmodified SnO₂ (16.4% PCE). This work provided fundamental insights into passivation mechanisms while showcasing the performance potential of properly designed fullerene derivatives [173].

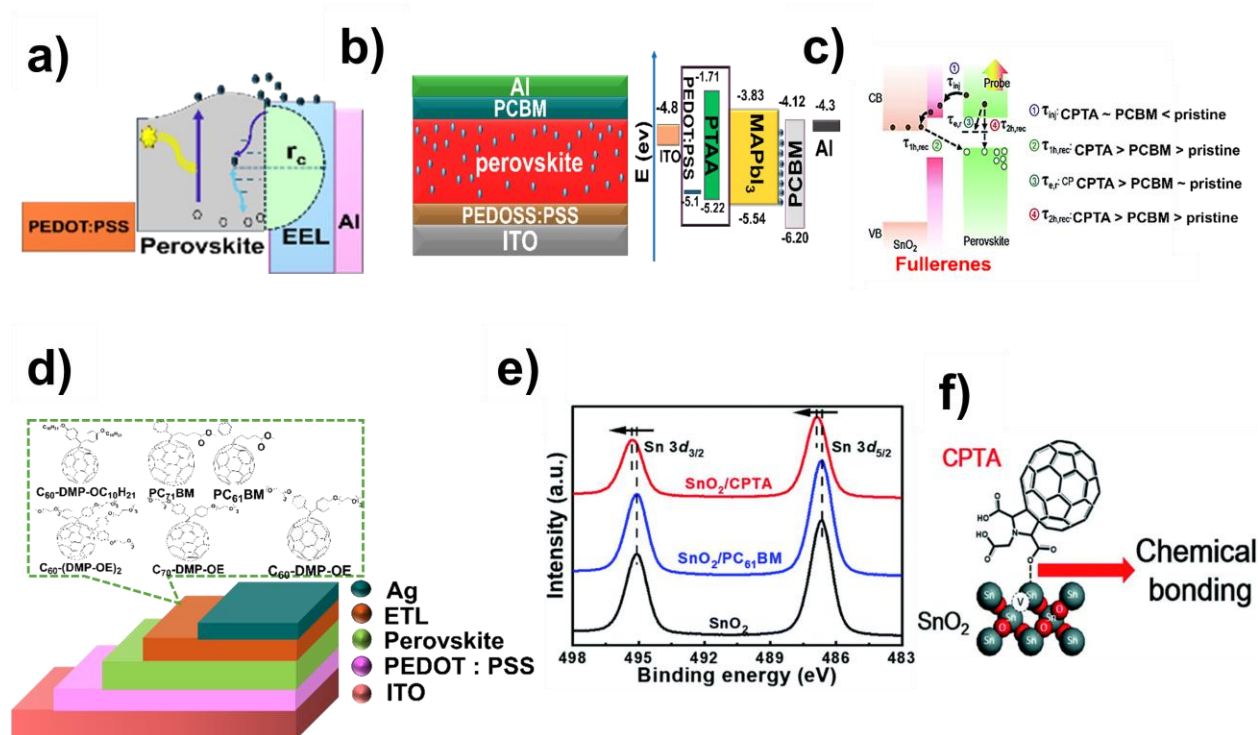


Figure 7. a) Suggested framework for the light-soaking effect[174], b)The architectural design of devices utilizing PSCs, encompasses the chemical compositions and energy states of various fullerene derivatives, c) Device architecture and their corresponding energy states diagram of the PSCs[175], d) the physical adhesion between the SnO₂ surface and PC61BM. Panel e) displays high-resolution XPS spectra of the Sn 3d core level for SnO₂, SnO₂/PC61BM, and SnO₂/CPTA films, and f) the chemical bond formation between the SnO₂ surface and CPTA[173].

4.5.3 Heterocyclic pyridine and thiophene functionalized fullerene derivatives

The electronic properties of fullerene-based ETMs can be precisely tuned through strategic incorporation of π -conjugated heterocycles like pyridine and thiophene (Figure 8a)[33]. These aromatic modifications serve dual rules: they optimize π - π stacking interactions between fullerene cages while introducing coordination sites for perovskite defect passivation. The curved geometry of C₆₀ provides an ideal platform for these functionalizations, where conjugated systems enhance

charge transport and flexible side chains prevent aggregation without compromising solubility, a critical balance for high-performance ETMs.

Zhou Xing and Yang et al. established a design paradigm for these materials through systematic development of pyrrolidine-based derivatives (C_{60} -HPy, C_{60} -BPy, C_{60} -MPy) (Figure 8b) [176]. Their work revealed two key structure-function relationships: (1) longer N-alkyl chains improve moisture resistance by encapsulating the perovskite layer, while (2) pyridine-Pb²⁺ coordination directly reduces interfacial defects (Figure 8c). This understanding enabled Yang's group to develop C_{60} -3-Py, where meta-positioned nitrogen sites achieved 17.57% PCE in MAPbI₃ devices through enhanced defect passivation [177]. The superiority of pyridine-functionalized ETMs becomes evident in comparative studies with conventional materials. Deng Xie's PCBBz demonstrated advantages over TiO₂ across multiple parameters, higher charge mobility, enhanced ELA, and improved wetting properties, culminating in 18.27% PCE[178]. These findings were extended to mixed-cation devices by Wang Ye, where C_{60} -3-BPy achieved 18.22% PCE in CsFAMA PSCs versus 15.70% for PCBM controls, attributed to improved energy level modulation and perovskite crystallization[179]. Zhu et al.'s work with C_{60} -BPy, Sn-based PSCs highlighted the versatility of this approach (Figure 8d). The strong Sn-pyridine interaction reduced surface trap density while optimizing energy alignment, yielding 14.14% PCE with exceptional light-soaking stability (95% retention after 1000 hours)[180]. This demonstrates how molecular modifications address both efficiency and stability challenges, a critical requirement for commercial viability (Figure 8e). As summarized in Table 3, these rationally designed derivatives outperform conventional fullerenes across multiple performance metrics while offering processing advantages.

Their development represents a significant step toward tailored interfacial materials that can address the complex requirements of high-efficiency, stable PSCs.

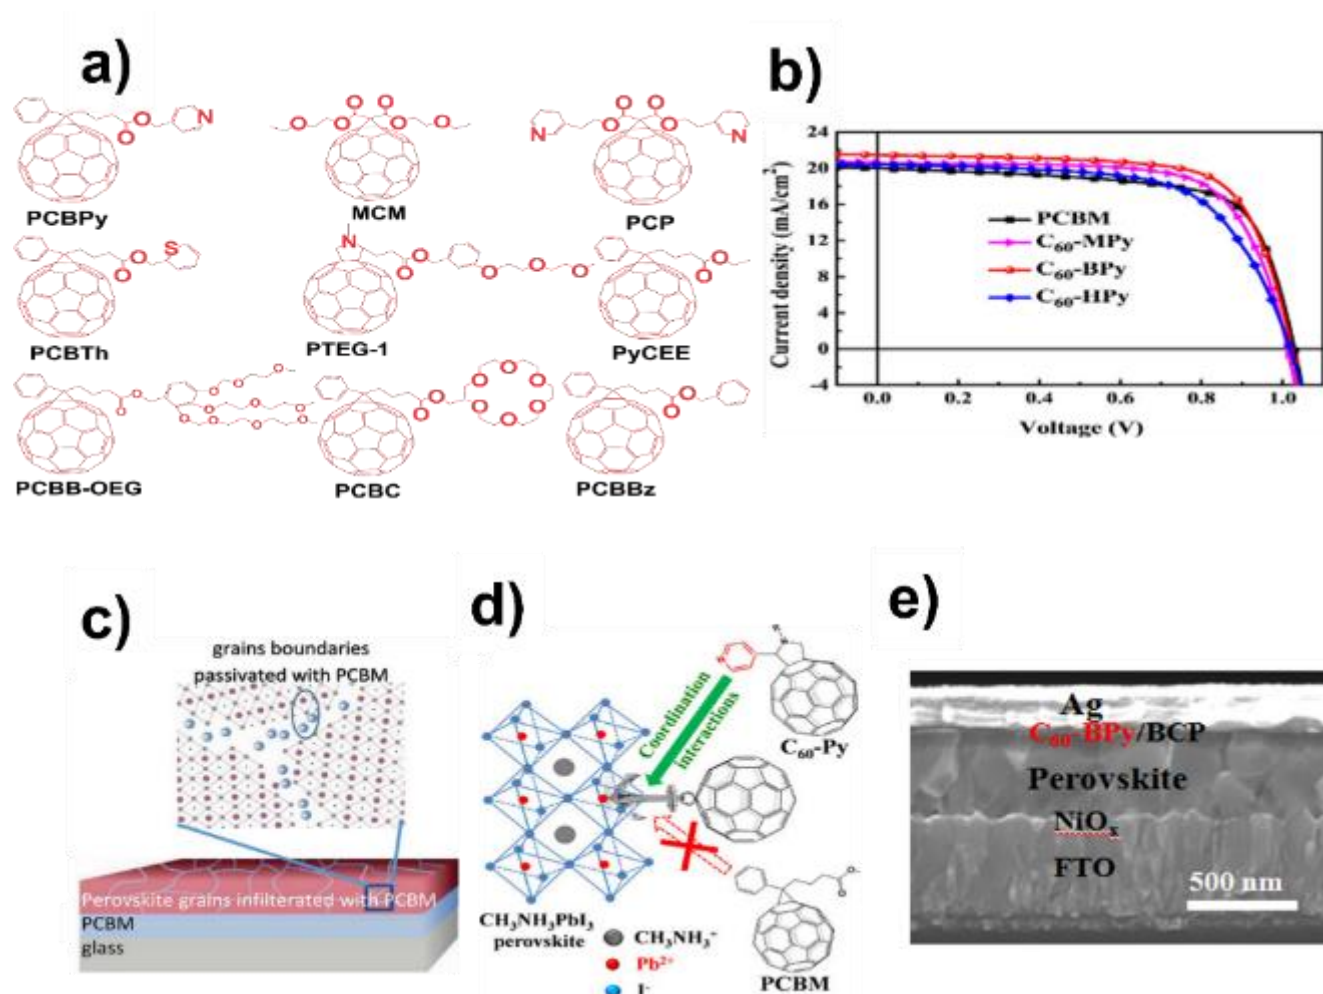


Figure 8. a) The molecular configurations of heterocyclic functionalized fullerene utilized in PSCs[154], b) *J-V* profiles of the control and C₆₀-Py ETM-based device, c) The device structure indicates the diffusion of PCBM molecules through the grain boundaries of the perovskite layer[22], d) Schematic demonstration of Interaction between light-harvesting layer and Fullerene ETMs[181], and e) SEM image of a device incorporating C₆₀-BPy as ETM.

A functionalized fullerene derivative, C₆₀-BPy, has shown promise in enhancing Sn-based PSCs by improving electron extraction, reducing interfacial recombination, and enhancing ELA[182]. Its integration also improves film quality and device stability (Figure 9a). In a subsequent development in 2019, Deng, Xie, and colleagues developed another novel pyridine-functionalized fullerene derivative, PyCEE, which was employed as an alternative to the conventional TiO₂ ETM in planar n-i-p PSCs (Figure 9(b,c)). Compared to TiO₂, the PyCEE ETM exhibits a less wettable surface, more favorable energy level alignment, higher electron mobility, and enhanced trap passivation through coordination interactions with Pb²⁺ ions in the CH₃NH₃PbI₃ film[183]. These properties facilitate the formation of large-grained perovskite films, improve electron extraction and transport, reduce hysteresis, and yield a champion PCE of 18.27%[178]. Beyond their use as ETMs in PSCs, the integration of heterocyclic pyridine- and thiophene-functionalized fullerene derivatives as additives within the perovskite layer offers an effective strategy for enhancing the performance of bulk heterojunction (BHJ) PSCs. In 2019, Lingbo Jia and his group developed a pyridine-functionalized fullerene derivative, C₆₀-PyP, [154] and incorporated it as an additive in the CH₃NH₃PbI₃ perovskite film of p-i-n PSCs. The addition of C₆₀-PyP reduced the nucleation Gibbs free energy and promoted controlled crystalline orientation, leading to enhanced crystallinity and a significant reduction in trap states (Figure 9d) [184]. This improvement stemmed from the coordination interaction between the nitrogen atom of the pyridine group and Pb²⁺ ions in the perovskite. Consequently, the optimized devices achieved a champion PCE of 19.82%, a substantial enhancement compared to control devices without the additive.

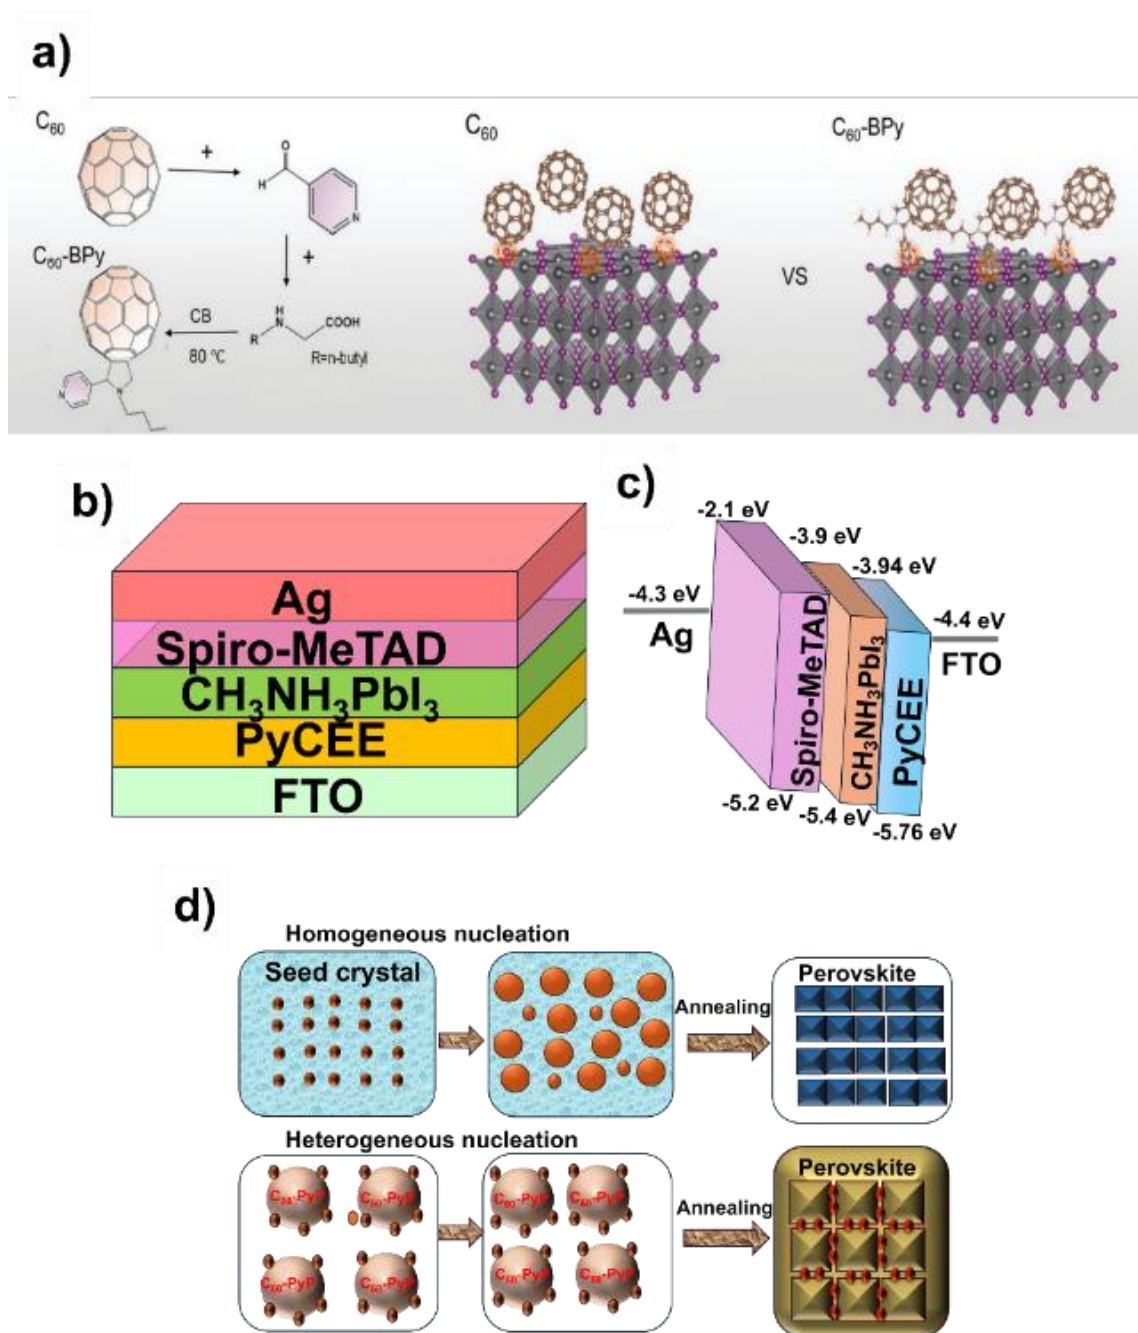


Figure 9. a) The structure of C₆₀-BPy and its schematic representation illustrate the interfacial interactions between the perovskite layer and C₆₀-BPy[180], b,c) Device structure of PyCEE and Energy level diagram, and d) Diagrammatic representation of perovskite nucleation with and without C₆₀-PyP[184].

4.7 Fullerene Derivatives with Carboxyl and Hydroxyl Groups

4.7.1 Carboxyl functionalized fullerene derivatives/ carboxylate (COOH) fullerene derivatives.

The inherent limitations of MO ETMs in planar PSCs, particularly oxygen vacancy-related defects that hinder charge transport, have spurred the development of carboxyl-functionalized fullerene derivatives as interfacial modifiers, (Figure 10a). These materials address two critical challenges simultaneously: passivating surface defects while optimizing ELA (Figure 11a). Snaith et al. pioneered this approach with C₆₀-SAM, a carboxylated fullerene self-assembled monolayer that reduced trap-assisted recombination at TiO₂ interfaces, achieving 17.3% PCE in mixed-halide perovskites with minimal hysteresis [185]. The success of this strategy stems from the dual functionality of carboxyl groups anchoring firmly to metal oxide surfaces while passivating perovskite defects through coordination with Pb²⁺ ions. This concept has been expanded through various molecular designs. Mora-Seró's cyano-carboxyl fullerene derivatives demonstrated how combining multiple functional groups (COOH and -CN) could further reduce capacitive hysteresis, yielding 13.5% PCE. Bo et al. showed that even simple carboxylation (PCBA) could boost TiO₂-based devices to 17.76% PCE with a remarkable 1.16V Voc, highlighting the universal effectiveness of carboxyl anchoring [157].

The most significant advances emerged from CPTA-based systems, where carboxyl groups were leveraged for electronic and crystallographic control. Jia et al established CPTA as a high-performance ETM (18.39% PCE on glass) [154], while Xu demonstrated its stability-enhancing properties on SnO₂. Wang's breakthrough CPTA:PbI₂ template system (20.20% PCE) revealed the profound impact of carboxyl coordination on perovskite nucleation, the octahedral Pb²⁺-CPTA

complexes reduced nucleation barriers[141], producing large-grained films with exceptional uniformity (FF >80%). This epitaxial growth mechanism represents a paradigm shift in perovskite crystallization control.

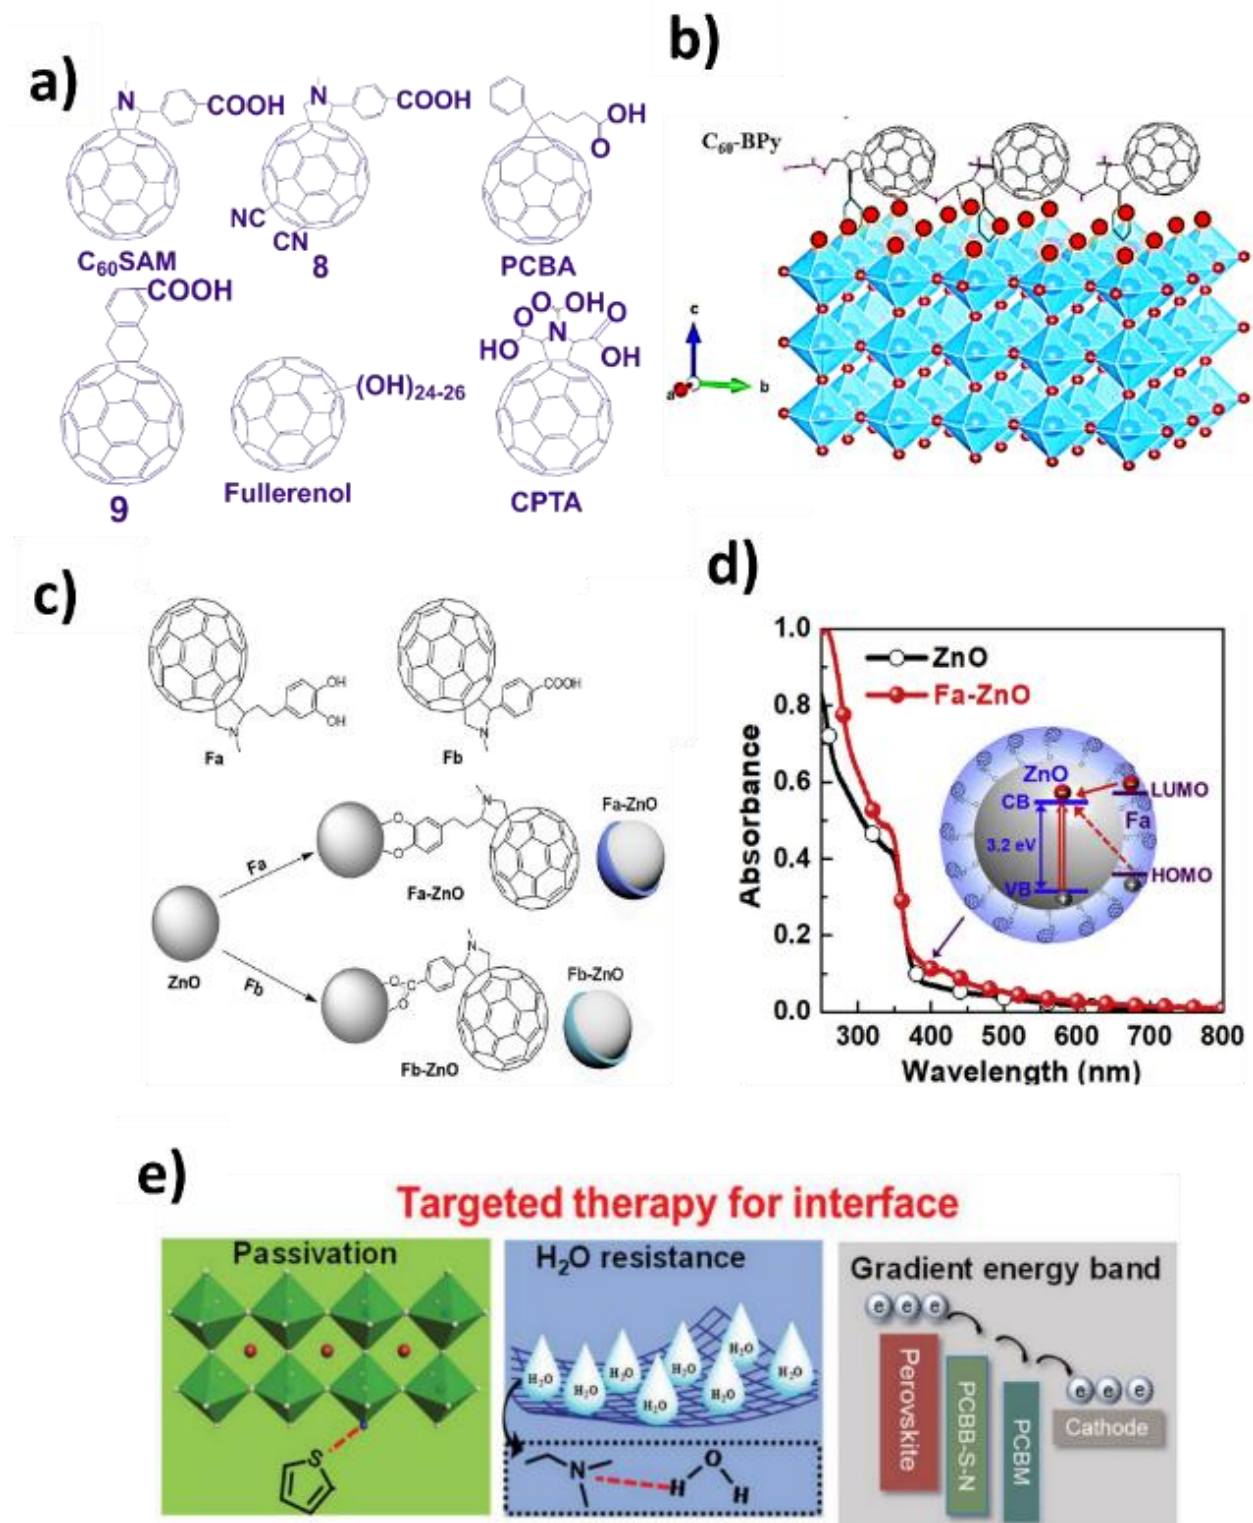


Figure 10. a) The molecular architectures of functionalized fullerene featuring carboxyl and hydroxyl groups, which are applied in PSCs[154], b) The illustration depicting the interaction

between perovskite materials and fullerene derivatives[140], c) schematic demonstration that details the coating of fullerene derivatives on ZnO nanoparticles characterized by core-shell configurations,d) an illustration of the functions of PCBB-S-N [186], and e) analysis of the UV-visible absorption spectra of the pertinent films characterized by core-shell configurations[187].

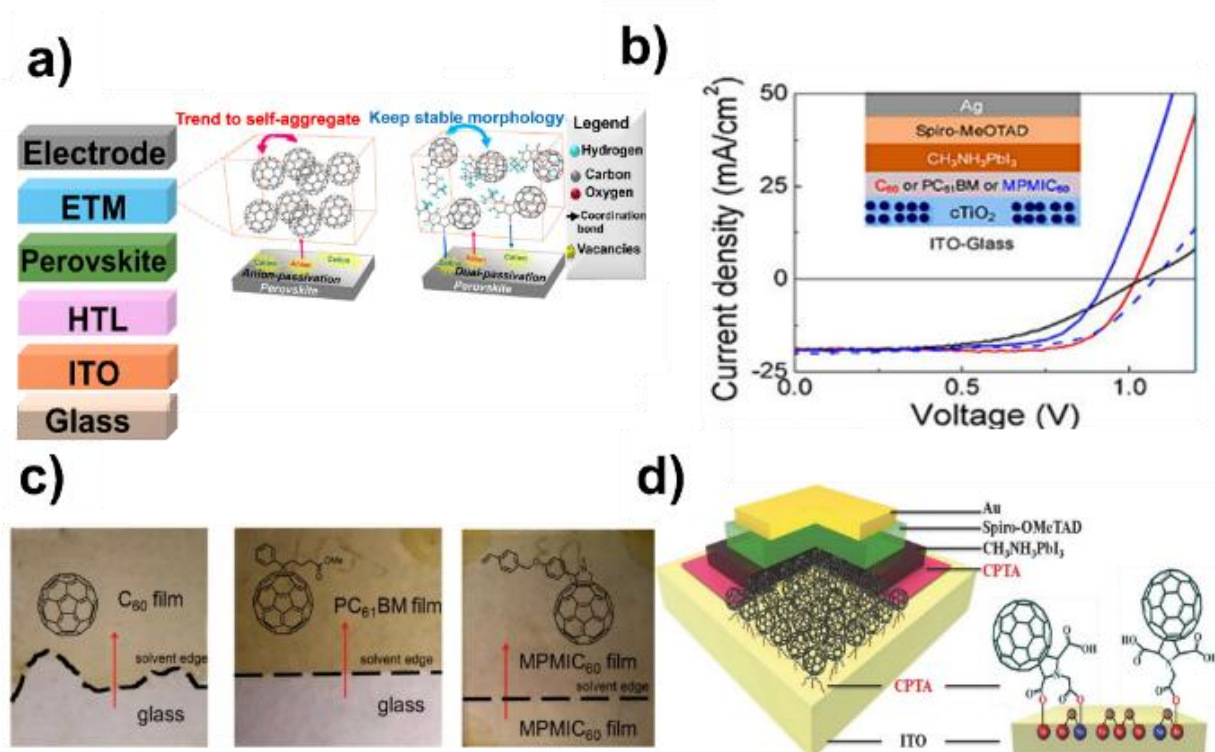


Figure 11. a) Performance assessment of FIDO and C₆₀ in PSC applications[147], b) The J-V characteristics of PSCs employing cross-linked MPMIC₆₀, PCBM, or C₆₀ as ETMs[160] ,c) Solvent resistance analysis of cured C₆₀, PC₆₁BM, and MPMIC₆₀ films[30], and d) A diagrammatic representation of the device architecture for planar n-i-p PSC featuring CPTA as ETM[129].

4.7.2 Hydroxyl (-OH) functionalized fullerene derivatives

Hydroxyl groups have emerged as versatile polar anchors for tailoring fullerene-based interfacial layers in PSCs, complementing the more established carboxyl-functionalized analogues. Chen et al.'s pioneering 2016 work with fullerenol (Figure 10a) demonstrated how multiple -OH groups could simultaneously enhance TiO_2 conductivity and perovskite wettability, establishing a template for subsequent developments [188]. The material's hydrophilic nature improved interfacial contact while its electron-rich structure facilitated charge transport, addressing two critical limitations of oxide-based ETMs.

The functionality of hydroxyl groups was further expanded through innovative molecular designs. Zhan et al. developed a hydrophobic C₉ derivative combined with a long alkyl chain with strategic -OH placement, achieving 21.3% PCE [189] in mixed-cation devices through dual action: (1) covalent bonding with undercoordinated Sn atoms passivated oxygen vacancies, while (2) the hydrophobic backbone protected the perovskite layer. This concept was refined in Chen's 2019 NPC₆₀-OH, where phenolic-OH-OH-OH-OH groups optimized the SnO_2 /perovskite interface, reducing the energy barrier while enlarging perovskite grains (21.39% PCE) [190]. The most sophisticated implementation came from Jen's catechol-functionalized Fa, which formed Zn-O-C bridges with ZnO nanoparticles (Figure 10c). This quasi-core-shell structure (Fa-ZnO NPs) (Figure 11c), uniquely enhanced electron density in ZnO's conduction band through interfacial charge redistribution, demonstrating how hydroxyl chemistry can fundamentally modify oxide electronic properties (Figure 10e) [191].

While carboxyl and hydroxyl groups share similar anchoring capabilities, hydroxyl-functionalized derivatives offer distinct advantages in moisture-sensitive applications due to their reduced acidity. The optimal spatial arrangement of these polar groups, whether in densely

functionalized fullerenols or strategically placed single -OH units, remains an important area for future investigation, particularly for achieving both high efficiency (>22%) and long-term operational stability in PSCs.

4.8 Fullerene Derivatives with Halogen.

Halogen-functionalized fullerene derivatives (Figure 10) have emerged as vital components in enhancing the performance and stability of PSCs. The incorporation of halogen atoms into the fullerene structure effectively tunes the electronic characteristics, particularly influencing the HOMO/LUMO energy levels.[192]. This adjustment facilitates better ELA between the ETM and adjacent layers, promoting more efficient photoinduced charge transfer dynamics. Moreover, halogenation enhances the interfacial interaction and surface properties of the ETM and light-absorbing layers, which collectively contribute to improved film morphology, reinforced lattice integrity, and a reduction in interfacial defect density. These improvements are instrumental in suppressing non-radiative recombination pathways and elevating device efficiency.

Halogenated fullerene derivatives also act as effective passivation agents, mitigating both surface and interface defects that commonly lead to charge carrier recombination. Their inherent chemical robustness provides additional protection against environmental degradation, particularly from moisture and oxygen. Furthermore, these derivatives enhance charge carrier dynamics by extending carrier lifetime and improving mobility, thereby facilitating more efficient charge extraction and collection. For instance, Liu et al. investigated the influence of halogen substitutions, specifically hydrogen (H), chlorine (Cl), and bromine (Br), on fullerene derivatives and observed enhanced crystallinity in the perovskite layer, increased grain size, and reduced grain boundary density[193]. Notably, the incorporation of NAMF-Cl, which induces chlorination of the TiO₂

layer, promoted stronger Ti–Cl bonding and yielded a power conversion efficiency (PCE) of 19.2%. Similarly, Rajagopal et al. utilized a difluorinated fullerene derivative (DF-C₆₀) in the fabrication of lead-tin (Pb-Sn) binary PSCs with a narrow bandgap structure. By employing an anti-solvent method, they achieved a graded heterojunction within the perovskite film. This strategy effectively suppressed deep-state defects and improved perovskite quality, culminating in a PCE of 15.61% [194].

4.9 Cross-linked fullerene derivatives

Fullerene derivatives are generally solubilized in organic solvents and subsequently harnessed onto the light-harvesting layer during device fabrication. However, this method can lead to the partial dissolution of both the charge collection layer and the perovskite layer, adversely affecting overall device performance. To address this issue, cross-linkable fullerene derivatives have been developed, significantly enhancing the stability of ETMs. These derivatives typically incorporate highly reactive functional groups such as styryl, vinyl, silyloxy, oxetane, thiophene, and benzocyclobutene etc. The crosslinking mechanisms for these groups rely on free radical or ionic reactions, triggered by stimuli such as thermal energy, UV light, or chemical initiators. Specifically, heating can induce polymerization in fullerene derivatives with styryl, vinyl, siloxyl, azide, and benzocyclobutane functionalities. Oxetane groups are known to undergo ring-opening polymerization when subjected to UV curing, creating robust cross-linked networks.

Additionally, azide groups, characterized by their highly reactive nitrogen atom, facilitate cross-linking reactions, further enhancing the structural integrity and solvent resistance of fullerene-based ETMs.

Zang et al. demonstrated the effectiveness of cross-linking as a modification strategy for fullerene-based ETMs. They developed a tailored fullerene derivative capable of forming an insoluble, interconnected network in aprotic solvents. This network not only preserves high electron mobility but also enhances resistance to solvent-induced dissolution, thereby significantly improving the long-term operational stability of the device [112].

4.9.1 Thermal cross-linked (TCL) fullerene derivatives

To enhance device performance, it is essential to address the challenges encountered by other ETMs, including inadequate surface morphology (Figure 11a), misalignment of energy levels, and insufficient adhesion to the light-harvesting layer. Watson et al. conducted an early investigation into a cross-linkable fullerene derivative known as 1-(p-phenoxy) -(p-methylvinylbenzene)-indolino fullerene (MPMIC₆₀), capable of achieving complete cross-linking upon heating to 250°C [121]. Their findings demonstrated that cross-linked MPMIC₆₀ significantly improves solvent resistance and raises the fracture energy of the TiO₂ ETM compared to traditional PCBM and C₆₀ films, (Figure 11b), achieving a PCE of 13.8 %. Snaith and co-workers, in 2016, incorporated two distinct cross-linked fullerene variants, namely PCBCB and sol-gel C₆₀, into PSCs. Sol-gel C₆₀ underwent cross-linking via hydrolysis-condensation reactions, while PCBCB was cross-linked through thermal annealing at 200°C. Both processes resulted in insoluble films with improved electron-selective interfaces, reduced shunting pathways, enhanced hole-blocking properties, and optimized charge carrier dynamics, leading to a significant PCE of 17.9%.

Hong et al developed another fullerene derivative, C-PCBSD (Figure 12a), functionalized for use as a TCL, employing an anti-solvent deposition technique for integration into perovskite films. This approach improved perovskite crystallization, electron extraction efficiency, and

resulted in a PCE of 17.21% [195]. Building on this approach, the authors further developed a composite film composed of C-PCBSD and graphdiyne (GD), formed via π - π stacking interactions. This composite exhibited enhanced electron mobility, improved energy-level alignment, and facilitated the growth of high-quality perovskite layers with increased resistance to solvent exposure. As a result, the device achieved a significantly improved PCE of 20% along with enhanced operational stability. Additionally, Kang et al. introduced a UV-curable cross-linked fullerene derivative, C-PCBOD, which was employed to modify the TiO₂ electron transport layer [196]. The resulting cross-linked PCBOD film (Figure 12b) demonstrated excellent surface coverage on TiO₂ and formed a robust hydrophilic protective layer (Figure 12c), effectively preventing solvent-induced damage during the deposition of the CH₃NH₃PbI₃ perovskite absorber (Figure 12d).

Furthermore, a styrene functionalized cross-linkable fullerene derivative, MPMIC₆₀, was developed as an alternative to conventional ETMs like PCBM and C₆₀ (Figure 11c). Upon annealing at 250°C, MPMIC₆₀ formed a solvent-resistant film with enhanced rupture toughness, resulting in substantial improvements in V_{oc} and J_{sc}. Giacalone et al. enhanced fullerene derivatives by incorporating PCL silane molecules through substituting benzoic acid groups (Figure 12e) [197]. Silane features three –OH groups in their structure. one interacts through hydrogen bonding with the –COOH group present in the C₆₀ self-assembled monolayer (C₆₀-SAM), while the remaining two –OH groups partake in coupling reactions forming Si–O–Si bonds (Figure 12f). Furthermore, introducing hydrophobic trifluoromethyl groups into silane molecules significantly enhances the water resistance of the fullerene layer[198].

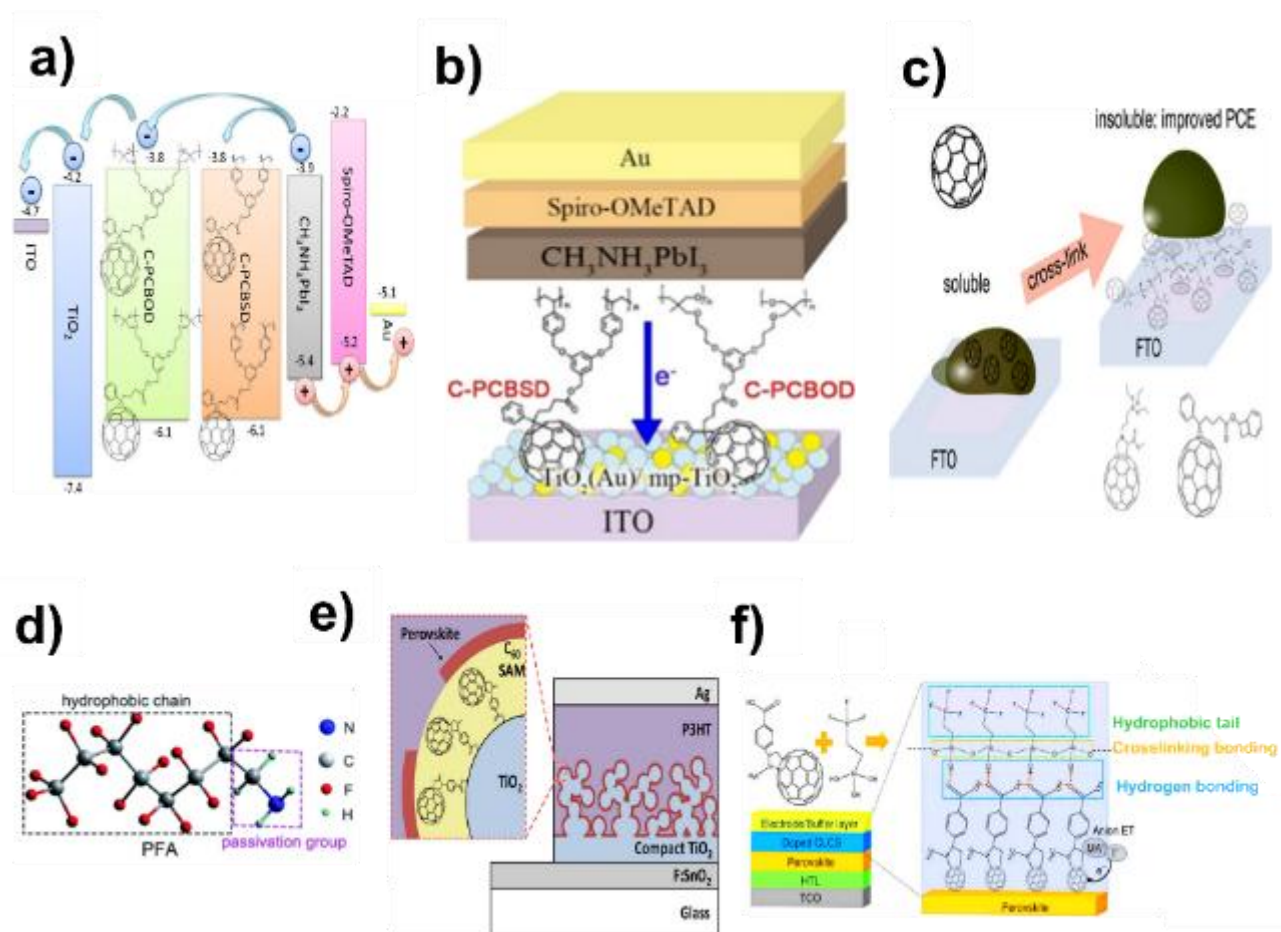


Figure 12. a) Schematic representation of a PSC with energy levels associated with each layer [196], b) Passivation mechanism of C-PCBOD as an interfacial layer between TiO_2 and perovskite, c) The molecular architectures of cross-linked and halogen functionalized fullerene [187], d) Molecular structure of PFA [150], e) Diagram of the device architecture, showing C_{60} -SAM binding to the TiO_2 surface and its crosslinking with a silane-coupling agent [154, 187].

4.9.2 Photo cross-linked (PCL) fullerene derivatives

Fullerene derivatives are widely employed as organic ETMs in PSCs. However, their porous molecular structure raises concerns due to their susceptibility to moisture-induced degradation. Researchers developed TCL of functionalized fullerene with styrene moieties is widely utilized for generating active sites, while epoxy groups can undergo light-induced cross-linking.

In 2017, Cabrera-Espinoza. introduced a novel functionalized fullerene designed as a cross-linkable agent for TiO_2 surface modification[199]. The UV-cured cross-linked PCBOD film notably improved surface coverage on the TiO_2 ETM, forming a moisture-resistant protective The cross-linked PCBOD interlayer effectively passivated DSs within the TiO_2 , enhancing electron separation and reducing charge recombination rates, thereby achieving impressive PCEs of 18.3% and 15.9%, respectively.

Cross-linkable fullerene derivatives, specifically the [6,6]-phenyl-C61-butyric styryl dendron (PCBSD) and the [6,6]-phenyl-C61-butyric oxetane dendron (PCBOD)[200]. These derivatives feature multiple cross-linking groups, allowing the formation of robust, highly cross-linked films on TiO_2 surfaces with exceptional coverage, superior solvent resistance, improved electron mobility, and effective passivation of surface defects. Devices using PCBOD-modified planar and mesoporous TiO_2 ETM achieved outstanding PCE of 15.9% and 18.3%, respectively. Cross-linking strategy utilizing 1,6-diazidohexane (DAZH) to link PCBM molecules, forming cross-linked PCBM through nitrene and C–H activation reactions.[121]. This cross-linked PCBM interlayer, applied on top of the TiO_2 ETM, exhibited outstanding electron extraction properties and robust solvent resistance, thereby preventing the perovskite precursor from being displaced during spin-coating. Consequently, PSCs with the composition $(\text{HC}(\text{NH}_2)_2)_{0.66}(\text{CH}_3\text{NH}_3)_{0.34}\text{-PbI}_{2.85}\text{Br}_{0.15}$ achieved PCEs of 18.4% for smaller devices and 14.9% for 4 cm^2 modules.

4.10 ICBA and ICBA-like fullerene derivatives.

While PCBM remains a widely used ETM in PSCs, its limitations in ELA and interfacial recombination have spurred the exploration of alternative fullerene derivatives, notably indene- C_{60} bisadduct (ICBA) and its analogues, (Figure 13a). These materials offer tunable lowest unoccupied molecular orbital (LUMO) levels, enhanced solubility, and improved defect passivation capabilities, addressing key challenges in PSC performance[201]. Recent studies highlight the superiority of ICBA-like derivatives over conventional PCBM. Voc was optimized by introducing 4-fluoro phenethylamine hydrobromide (FPEABr) as a dipole layer, (Figure 13b), aligning energy levels at the perovskite/ICBA interface, and achieving a PCE of 15.7% [202].

Xing et al. incorporated ICBA into perovskite precursors, passivating grain boundary defects and enhancing charge extraction, achieving a PCE of 18.14% (Figure 13c)[142]. The introduction of ICBA into the perovskite grain boundaries facilitated the photocarrier dynamics of charge carriers from the perovskite layer to the ETMs, leading to an increased PCE of 18.14%. This approach allowed for a more effective alignment of the energy levels between the absorber and ICBA layers, resulting in a unilateral increase in the device's Voc by one-tenth, ultimately leading to an impressive PCE record of 15.7% [203].

T.Ji et al [204] reported a modest PCE of 3.4% with ICBA, later improved to 8.06% by Jen et al. via bis- C_{60} doping[131]. ICBA-trans in wide-bandgap PSCs, achieving a PCE of 18.5% and Voc of 1.21 V due to reduced energy disorder.[204]. The P3HT/ICBA-based cell has demonstrated notable performance metrics, achieving a PCE of 6.22%, a V_{oc} of 0.84 V, and a J_{sc} of 12.4 mAcm^{-2} (Figure 13d). Additionally, Neher et al. demonstrated that indene- C_{60} -tris adduct (ICTA) has higher LUMO level (-3.36 eV vs. PCBM's -3.9 eV) reduces energy loss, enhancing

Voc, though reduce charge extraction efficiency[205]. Cao et al. developed C₆₀(CH₂)(Ind), which enhanced defect passivation and electron extraction (PCE: 18.1%, Voc: 1.13 V) [206].

Yang et al. synthesized C5-NCMA, achieving a PCE of 17.6% via high LUMO alignment[207]. Xie et al. compared derivatives EBNC (7.36%) and EDNC (12.64%), noting lower efficiencies than PCBM due to suboptimal functional groups[208]. To improve the structural stability, Albrecht et al. observed that TiO₂/PCBM bilayers (PCE: 18.0%) outperform ICMA (13.9%) due to superior ELA in wide-bandgap PSCs ($E_g \approx 1.8$ eV), Li et al. achieved a Voc of 1.35 V and PCE of 18.9% using CMC: ICBA blends (Figure 13e), with minimal non-radiative losses ($\Delta V_{oc} = 70$ mV) [209]. Although significant advancements have been achieved with ICBA, its effectiveness is hindered by its low electron mobility ($\sim 10^{-4}$ cm².V⁻¹.s⁻¹) is significantly lower than PCBM's ($\sim 10^{-2}$ cm².V⁻¹.s⁻¹), limiting charge extraction in thick films. These factors significantly impede the effective transport of charge carriers from the light-harvesting layer to the ETM.

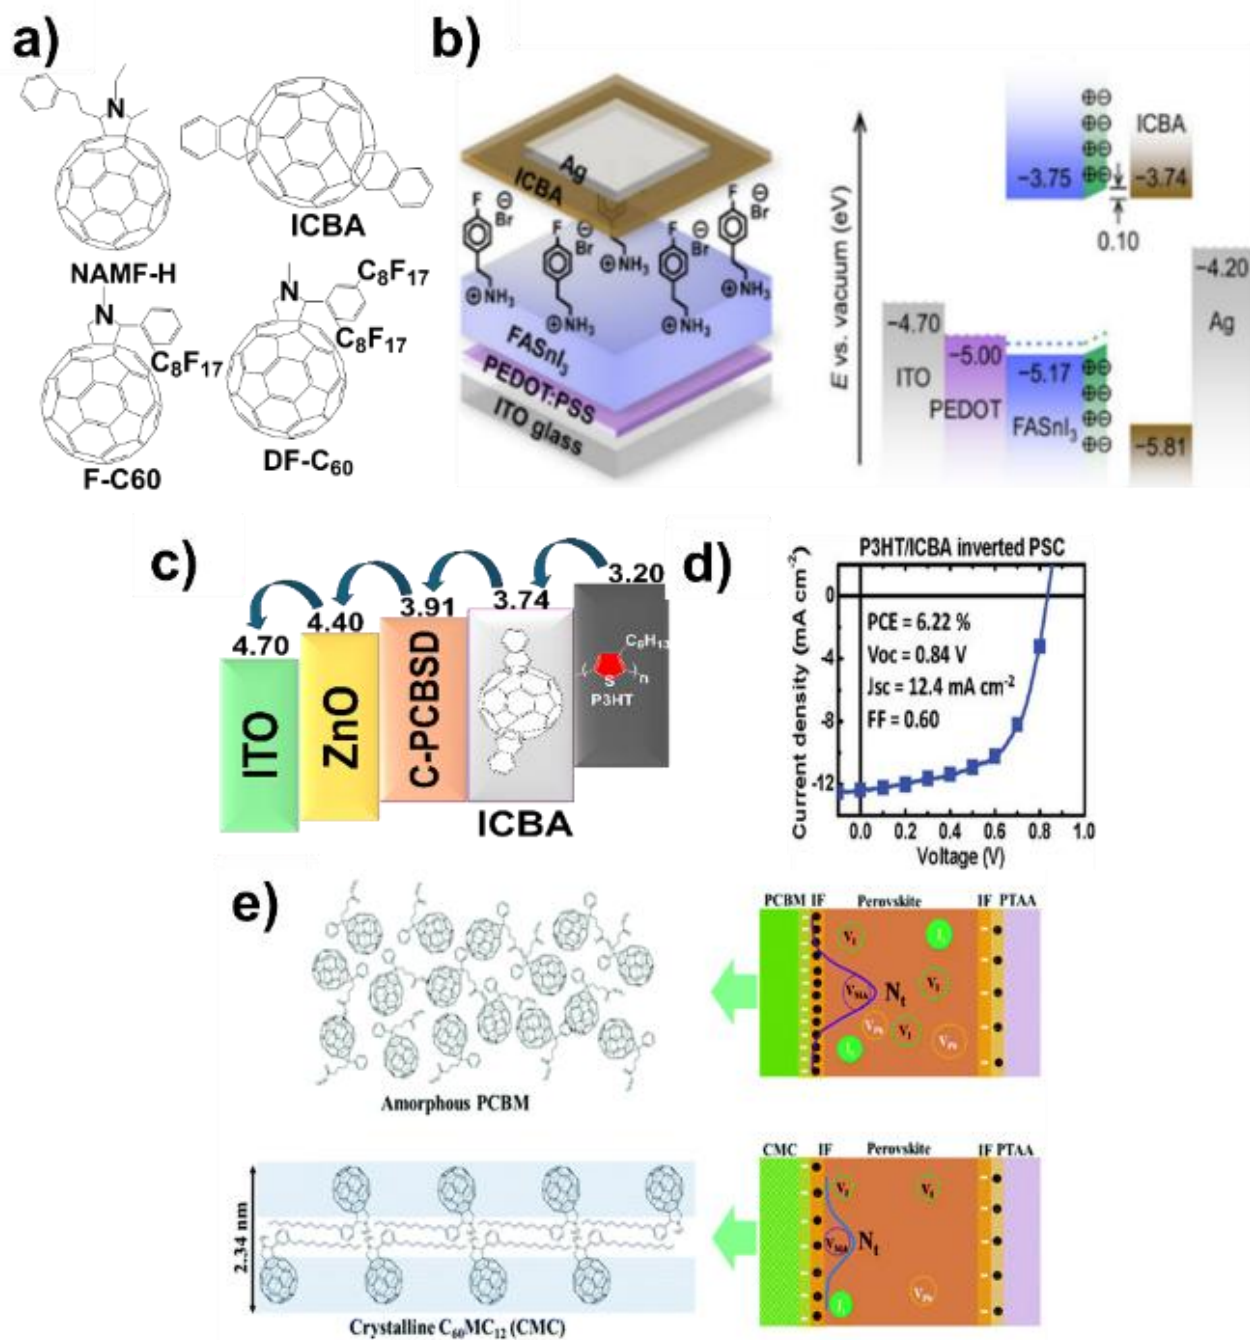


Figure 13. a) Molecular structure of ICBA derivatives[203], b) Schematic depiction of the mechanism involving crystalline fullerene derivatives for enhancement in device performance[154], (c, d) Structure and energy levels of the inverted PSC, and e) the multilayer configurations energy levels diagram, and their corresponding J-V curve.

5. Conclusions and outlook

Functionalized fullerenes have played a transformative role in advancing the efficiency and stability of PSCs, particularly through the modulation of photocarrier dynamics. Derivatives such as PCBM, and ICBA have demonstrated multifunctionality-acting not only as efficient ETMs but also as interfacial passivators that mitigate defect states and enhance charge separation. These attributes have enabled PSCs to achieve power conversion efficiencies exceeding 24%, while simultaneously improving operational stability. Spectroscopic investigations have confirmed their capability to coordinate with perovskite lattices, reduce non-radiative recombination, and facilitate robust charge transport.

Despite these achievements, several challenges remain unresolved. The impact of specific functional groups on long-range charge diffusion and electronic coupling remains poorly understood, limiting further optimization of device performance. Interfacial issues such as aggregation and energy-level mismatch continue to hinder charge extraction and promote recombination, particularly in large-area or flexible architectures. Moreover, the absence of systematic design principles for fullerene functionalization restricts the rational development of derivatives tailored to diverse PSC configurations.

In light of these limitations, non-fullerene ETMs, such as cyano-functionalized bithiophene imide dimer (CNI2)-based polymers (e.g., PCNI2-BTI), offer several advantages, including excellent photothermal stability, high electron mobility, good solubility, and strong interfacial interactions with perovskite layers. These attributes have enabled the realization of PCEs exceeding 26% along with outstanding device stability, positioning non-fullerene ETMs as highly competitive alternatives to their fullerene-based counterparts. To address current limitations and drive further progress in ETM development, future research should focus on the molecular

engineering of materials with tailored energy levels, enhanced passivation properties, and improved morphological compatibility. Moreover, the exploration of hybrid systems that integrate the interfacial stability of fullerene derivatives with the tunability and multifunctionality of non-fullerene materials holds significant promise. The application of advanced spectroscopic and computational techniques will also be crucial for elucidating charge transport and recombination mechanisms, thereby facilitating predictive design strategies optimized for specific device architectures.

Author Information

Corresponding authors

*Email: KHADKA.B.Dhruba@nims.go.jp (D.B.K.)

*Email: ycwang@mail.nsysu.edu.tw (Y.-C.W.)

ORCID

Dhruba B. Khadka: 0000-0001-9134-3890

Ying-Chiao Wang: 0000-0002-6459-0770

Author Contributions

Muhammad Waqas: conceptualization, visualization, writing – original draft. Dhruba B. Khadka: supervision, writing – review and editing. Abdul Haseeb Hassan Khan: literature organizing, categorizing. Ying-Chiao Wang: conceptualization, funding acquisition, supervision, writing – review and editing.

Conflicts of Interest

The authors declare no competing financial interest.

Acknowledgments

Y.-C.W. acknowledges the financial support from the National Science and Technology Council (NSTC), Taiwan, R.O.C. (Grant No. NSTC 113-2221-E-110-005- and NSTC 112-2222-E-110-004-). This work was also supported by the Taiwan Comprehensive University System (TCUS). And Y.-C.W. thanks the Yushan Fellow Program by the Ministry of Education (MOE), Taiwan for the financial support.

References

- [1] S. Yang, W. Fu, Z. Zhang, H. Chen, and C.-Z. Li, "Recent advances in perovskite solar cells: efficiency, stability and lead-free perovskite," *Journal of Materials Chemistry A*, vol. 5, no. 23, p. 11462-11482, 2017.
- [2] R. Sharif *et al.*, "A comprehensive review of the current progresses and material advances in perovskite solar cells," *Nanoscale Advances*, vol. 5, no. 15, p. 3803-3833, 2023.
- [3] C. Zuo, H. J. Bolink, H. Han, J. Huang, D. Cahen, and L. Ding, "Advances in perovskite solar cells," *Advanced Science*, vol. 3, no. 7, p. 1500324, 2016.
- [4] T. Nie, Z. Fang, X. Ren, Y. Duan, and S. Liu, "Recent advances in wide-bandgap organic–inorganic halide perovskite solar cells and tandem application," *Nano-Micro Letters*, vol. 15, no. 1, p. 70, 2023.
- [5] F. Znidi, M. Morsy, and M. N. Uddin, "Navigating challenges and solutions for metal-halide and carbon-based electrodes in perovskite solar cells (NCS-MCEPSC): An environmental approach," *Heliyon*, vol. 10, no. 12, p. e32843, 2024.
- [6] P. Roy, N. K. Sinha, S. Tiwari, and A. Khare, "A review on perovskite solar cells: Evolution of architecture, fabrication techniques, commercialization issues and status," *Solar Energy*, vol. 198, p. 665-688, 2020.
- [7] D. Meng, J. Xue, Y. Zhao, E. Zhang, R. Zheng, and Y. Yang, "Configurable organic charge carriers toward stable perovskite photovoltaics," *Chemical Reviews*, vol. 122, no. 18, p. 14954-14986, 2022.
- [8] J. Lian, B. Lu, F. Niu, P. Zeng, and X. Zhan, "Electron-transport materials in perovskite solar cells," *Small Methods*, vol. 2, no. 10, p. 1800082, 2018.
- [9] V. S. Katta, M. Waheed, and J. H. Kim, "Recent advancements in enhancing interfacial charge transport for perovskite solar cells," *Solar RRL*, vol. 8, no. 7, p. 2300908, 2024.
- [10] P. W. Liang, C. C. Chueh, S. T. Williams, and A. K. Y. Jen, "Roles of fullerene-based interlayers in enhancing the performance of organometal perovskite thin-film solar cells," *Advanced Energy Materials*, vol. 5, no. 10, p. 1402321, 2015.
- [11] Y. Y. Lai, Y.-J. Cheng, and C.-S. Hsu, "Applications of functional fullerene materials in polymer solar cells," *Energy & Environmental Science*, vol. 7, no. 6, p. 1866-1883, 2014.
- [12] X.-J. Kong, L.-S. Long, Z. Zheng, R.-B. Huang, and L.-S. Zheng, "Keeping the ball rolling: fullerene-like molecular clusters," *Accounts of Chemical Research*, vol. 43, no. 2, p. 201-209, 2010.
- [13] P. Schwerdtfeger, L. N. Wirz, and J. Avery, "The topology of fullerenes," *Wiley Interdisciplinary Reviews: Computational Molecular Science*, vol. 5, no. 1, p. 96-145, 2015.
- [14] Y. R. Yao, O. Fernandez-Delgado, and L. Echegoyen, "Fullerenes and their applications," in *Handbook of Carbon-Based Nanomaterials*: Elsevier, vol. 1, p. 19-158, 2021.
- [15] Z. C. Chen, Y.-Z. Tan, and S.-Y. Xie, "Fullerenes violating the isolated pentagon rule," in *Handbook of Fullerene Science and Technology*: Springer, vol. 1, p. 181-217, 2022.
- [16] J. Zhao, Q. Du, S. Zhou, and V. Kumar, "Endohedrally doped cage clusters," *Chemical Reviews*, vol. 120, no. 17, p. 9021-9163, 2020.
- [17] Y. Z. Tan *et al.*, "Chlorofullerenes featuring triple sequentially fused pentagons," *Nature Chemistry*, vol. 2, no. 4, p. 269-273, 2010.
- [18] Y. Zhang *et al.*, "Structural, electronic, and nonlinear optical properties of C₆₆H₄ and C₇₀Cl₆ encapsulating Li and F atoms," *ACS Omega*, vol. 6, no. 24, p. 16234-16240, 2021.

- [19] F. N. de Sousa, D. E. A. Rodrigues, F. M. de Vasconcelos, V. Meunier, and E. C. Girão, "Electronic properties of carbon nanostructures based on bipartite nanocage units," *Chemical Physics*, vol. 580, p. 112206, 2024.
- [20] A. Mahmoodpoor *et al.*, "Ionic liquid gating in perovskite solar cells with fullerene/carbon nanotube collectors," *Energy Technology*, vol. 10, no. 9, p. 2200485, 2022.
- [21] L. Feng, K.-Y. Wang, G. S. Day, and H.-C. Zhou, "The chemistry of multi-component and hierarchical framework compounds," *Chemical Society Reviews*, vol. 48, no. 18, p. 4823-4853, 2019.
- [22] R. Zahran and Z. Hawash, "Fullerene-based inverted perovskite solar cell: a key to achieve promising, stable, and efficient photovoltaics," *Advanced Materials Interfaces*, vol. 9, no. 35, p. 2201438, 2022.
- [23] Y. Fang, C. Bi, D. Wang, and J. Huang, "The functions of fullerenes in hybrid perovskite solar cells," *ACS Energy Letters*, vol. 2, no. 4, p. 782-794, 2017.
- [24] L. Fu, H. Li, L. Wang, R. Yin, B. Li, and L. Yin, "Defect passivation strategies in perovskites for an enhanced photovoltaic performance," *Energy & Environmental Science*, vol. 13, no. 11, p. 4017-4056, 2020.
- [25] Y. Zhong *et al.*, "Inhibition of ion migration for highly efficient and stable perovskite solar cells," *Advanced Materials*, vol. 35, no. 52, p. 2302552, 2023.
- [26] Y. Zhao, W. Zhou, Z. Han, D. Yu, and Q. Zhao, "Effects of ion migration and improvement strategies for the operational stability of perovskite solar cells," *Physical Chemistry Chemical Physics*, vol. 23, no. 1, p. 94-106, 2021.
- [27] J. Thiesbrummel *et al.*, "Ion-induced field screening as a dominant factor in perovskite solar cell operational stability," *Nature Energy*, vol. 9, no. 6, p. 664-676, 2024.
- [28] W. Zhang *et al.*, "Modular functionalization of carbon nanotubes and fullerenes," *Journal of the American Chemical Society*, vol. 131, no. 24, p. 8446-8454, 2009.
- [29] D. Pantarotto, N. Tagmatarchis, A. Bianco, and M. Prato, "Synthesis and biological properties of fullerene-containing amino acids and peptides," *Mini Reviews in Medicinal Chemistry*, vol. 4, no. 7, p. 805-814, 2004.
- [30] G. Zhou *et al.*, "Recent Progress on Cross-Linkable Fullerene-Based Electron Transport Materials for Perovskite Solar Cells," *ChemSusChem*, vol. 18, no. 3, p. e202401629, 2025.
- [31] H. Wang, C. Zhang, Y. Yao, C. Cheng, and K. Wang, "Non-Fullerene Organic Electron Transport Materials toward Stable and Efficient Inverted Perovskite Photovoltaics," *Small*, vol. 20, no. 43, p. 2403193, 2024.
- [32] H. Si, X. Zhao, Z. Zhang, Q. Liao, and Y. Zhang, "Low-temperature electron-transporting materials for perovskite solar cells: fundamentals, progress, and outlook," *Coordination Chemistry Reviews*, vol. 500, p. 215502, 2024.
- [33] H. Wang, Z. Zhang, C. Zhang, Y. Yao, and K. Wang, "Structural modification of fullerene derivatives for high-performance inverted perovskite solar cells," *Journal of Materials Chemistry A*, vol. 12, p. 22442-22457, 2024.
- [34] Y. Li *et al.*, "A review on morphology engineering for highly efficient and stable hybrid perovskite solar cells," *Journal of Materials Chemistry A*, vol. 6, no. 27, p. 12842-12875, 2018.
- [35] B. Chen, S. Wang, Y. Song, C. Li, and F. Hao, "A critical review on the moisture stability of halide perovskite films and solar cells," *Chemical Engineering Journal*, vol. 430, p. 132701, 2022.

- [36] L. Zang, C. Zhao, X. Hu, J. Tao, S. Chen, and J. Chu, "Emerging trends in electron transport layer development for stable and efficient perovskite solar cells," *Small*, vol. 20, no. 26, p. 2400807, 2024.
- [37] Y. C. Wang *et al.*, "Quantum-assisted photoelectric gain effects in perovskite solar cells," *NPG Asia Materials*, vol. 12, no. 1, p. 54, 2020.
- [38] Z. Xiao *et al.*, "Thin-film semiconductor perspective of organometal trihalide perovskite materials for high-efficiency solar cells," *Materials Science and Engineering: R: Reports*, vol. 101, p. 1-38, 2016.
- [39] H. Lu *et al.*, "High-Quality PEI/Ag/PEI-Zn Semitransparent Electrode for Efficient ITO-Free Flexible Organic Solar Cells and Perovskite Solar Cells," *IEEE Journal of Photovoltaics*, vol. 15, no. 1, p. 46-53, 2024.
- [40] L. V. T. Merino *et al.*, "Impact of the valence band energy alignment at the hole-collecting interface on the photostability of wide band-gap perovskite solar cells," *Joule*, vol. 8, no. 9, p. 2585-2606, 2024.
- [41] T. Wang, W. Deng, J. Cao, and F. Yan, "Recent progress on heterojunction engineering in perovskite solar cells," *Advanced Energy Materials*, vol. 13, no. 33, p. 2201436, 2023.
- [42] P. Murugan, T. Hu, X. Hu, and Y. Chen, "Advancements in organic small molecule hole-transporting materials for perovskite solar cells: past and future," *Journal of Materials Chemistry A*, vol. 10, no. 10, p. 5044-5081, 2022.
- [43] V. Manjunath, S. Bimli, P. A. Shaikh, S. B. Ogale, and R. S. Devan, "Understanding the role of inorganic carrier transport layer materials and interfaces in emerging perovskite solar cells," *Journal of Materials Chemistry C*, vol. 10, no. 42, p. 15725-15780, 2022.
- [44] S. Kumar *et al.*, "Recent advances in perovskite materials: exploring multifaceted properties for energy harvesting applications," *Ionics*, vol. 30, no. 9, p. 5159-5188, 2024.
- [45] S. Kumar *et al.*, "Recent advances in perovskite materials: exploring multifaceted properties for energy harvesting applications," *Ionics*, vol. 30, p. 1-30, 2024.
- [46] A. K. Jena, A. Kulkarni, and T. Miyasaka, "Halide perovskite photovoltaics: background, status, and future prospects," *Chemical Reviews*, vol. 119, no. 5, p. 3036-3103, 2019.
- [47] C. Dormann, M. F. Dollard, and M. A. Idris, "PSC; current status and implications for future research," *Psychosocial Safety Climate: A new work stress theory*, vol. 1 p. 431-449, 2019.
- [48] M. I. Omer *et al.*, "Two quasi-interfacial pn junctions observed by a dual-irradiation system in perovskite solar cells," *npj Flexible Electronics*, vol. 7, no. 1, p. 23, 2023.
- [49] D. Ramirez *et al.*, "Meso-superstructured perovskite solar cells: revealing the role of the mesoporous layer," *The Journal of Physical Chemistry C*, vol. 122, no. 37, p. 21239-21247, 2018.
- [50] C. Zhang *et al.*, "Exploring the Potential and Hurdles of Perovskite Solar Cells with pin Structure," *ACS Nano*, vol. 18, no. 47, p. 32299-32314, 2024.
- [51] A. K. Al-Mousoi and M. K. Mohammed, "Engineered surface properties of MAPI using different antisolvents for hole transport layer-free perovskite solar cell (HTL-free PSC)," *Journal of Sol-Gel Science and Technology*, vol. 96, p. 659-668, 2020.
- [52] S. Jiang *et al.*, "Interfacial Energetics Reversal Strategy for Efficient Perovskite Solar Cells," *Advanced Materials*, vol. 1 p. 2503110, 2025.
- [53] S. Aftab, H. H. Hegazy, M. Z. Iqbal, M. W. Iqbal, G. Nazir, and S. Hussain, "Recent advances in dynamic homojunction PIN diodes based on 2D materials," *Advanced Materials Interfaces*, vol. 10, no. 6, p. 2201937, 2023.

- [54] S. Bhattarai *et al.*, "A detailed review of perovskite solar cells: Introduction, working principle, modelling, fabrication techniques, future challenges," *Micro and Nanostructures*, vol. 172, p. 207450, 2022.
- [55] H. Wang *et al.*, "Reducing the Depletion Region Width at the Anode Interface via a Highly Doped Conjugated Polyelectrolyte Composite for Efficient Organic Solar Cells," *ACS Applied Materials & Interfaces*, vol. 16, no. 3, p. 3744-3754, 2024.
- [56] G. A. Sibin, P. Gayathri, T. Akila, R. Marnadu, and V. Balasubramani, "Manifestation on the choice of a suitable combination of MIS for proficient Schottky diodes for optoelectronics applications: A comprehensive review," *Nano Energy*, vol. 125, p. 109534, 2024.
- [57] M. Abbas, X. Xu, M. Rauf, and A. K. K. Kyaw, "A Comprehensive Review on Defects-Induced Voltage Losses and Strategies toward Highly Efficient and Stable Perovskite Solar Cells," in *Photonics*, vol. 11, no. 1, p. 87, 2024.
- [58] P. Kumar, V. K. Shukla, M. Kim, and R. Singh, "A comprehensive review on dark current in perovskite photodetectors: Origin, drawbacks, and reducing strategies," *Sensors and Actuators A: Physical*, vol. 369, p. 115076, 2024.
- [59] Y. Wang, Q. Song, D. Li, Y. Liu, Y. Wang, and Y. Chen, "Strategies for Suppressing Dark Current of Perovskite Photodiodes towards Reliable Optoelectronic Applications," *Journal of Materials Chemistry C*, vol. 12, p. 10775-10805, 2024.
- [60] A. Morteza Najarian, M. Vafaie, B. Chen, F. P. García de Arquer, and E. H. Sargent, "Photophysical properties of materials for high-speed photodetection," *Nature Reviews Physics*, vol. 6, no. 4, p. 219-230, 2024.
- [61] V. S. Menon and A. Krishnamoorthy, "Hole Selectivity of n-Type Molybdenum Oxide Carrier Selective Layer for Commercial and Emerging Thin-Film Photovoltaics: A Critical Analysis of Interface Energetics and Ensuant Device Physics," *Energy Technology*, vol. 11, no. 11, p. 2300608, 2023.
- [62] H. Zhang and N.-G. Park, "Progress and issues in pin type perovskite solar cells," *DeCarbon*, vol. 3, p. 100025, 2023.
- [63] K. Anoop and T. Ahip, "Recent advancements in the hole transporting layers of perovskite solar cells," *Solar Energy*, vol. 263, p. 111937, 2023.
- [64] J. Suo, B. Yang, and A. Hagfeldt, "Passivation strategies through surface reconstruction toward highly efficient and stable perovskite solar cells on nip architecture," *Energies*, vol. 14, no. 16, p. 4836, 2021.
- [65] J. Zhou *et al.*, "Highly efficient and stable perovskite solar cells via a multifunctional hole transporting material," *Joule*, vol. 8, no. 6, p. 1691-1706, 2024.
- [66] Z. Chen *et al.*, "Perovskite grain-boundary manipulation using room-temperature dynamic self-healing "ligaments" for developing highly stable flexible perovskite solar cells with 23.8% efficiency," *Advanced Materials*, vol. 35, no. 18, p. 2300513, 2023.
- [67] J. Park *et al.*, "Controlled growth of perovskite layers with volatile alkylammonium chlorides," *Nature*, vol. 616, no. 7958, p. 724-730, 2023.
- [68] C. Zhao *et al.*, "Stabilization of highly efficient perovskite solar cells with a tailored supramolecular interface," *Nature Communications*, vol. 15, no. 1, p. 7139, 2024.
- [69] X. Liu, T. Wu, C. Zhang, Y. Zhang, H. Segawa, and L. Han, "Interface energy-level management toward efficient tin perovskite solar cells with hole-transport-layer-free structure," *Advanced Functional Materials*, vol. 31, no. 50, p. 2106560, 2021.

- [70] T. A. Chowdhury, M. A. B. Zafar, M. S.-U. Islam, M. Shahinuzzaman, M. A. Islam, and M. U. Khandaker, "Stability of perovskite solar cells: issues and prospects," *RSC Advances*, vol. 13, no. 3, p. 1787-1810, 2023.
- [71] G. D. Tabi *et al.*, "Fluorinated polymer additives in Spiro-OMeTAD to improve the efficiency and stability of perovskite solar cells," *Chemical Engineering Journal*, vol. 482, p. 149062, 2024.
- [72] D. B. Khadka *et al.*, "Coordination Nanosheets Stabilizing Efficient Tin-Based Perovskite Solar Cells," *ACS Applied Materials & Interfaces*, vol. 17, no. 18, p.26813-26822, 2025.
- [73] G. G. Njema, J. K. Kibet, and S. M. Ngari, "A review of interface engineering characteristics for high performance perovskite solar cells," *Measurement: Energy*, vol. 2, p. 100005, 2024.
- [74] Y. Zhang *et al.*, "Gelation of hole transport layer to improve the stability of perovskite solar cells," *Nano-Micro Letters*, vol. 15, no. 1, p. 175, 2023.
- [75] V. S. Menon, S. Ganesan, R. K. Raman, A. Alagumalai, and A. Krishnamoorthy, "Halogen doping of p-type inorganic hole transport layer: electronic nature-based dopant engineering for modulating hole selectivity in inverted planar perovskite solar cells," *Journal of Materials Chemistry C*, vol. 12, no. 20, p. 7306-7324, 2024.
- [76] S. Akel, A. Kulkarni, U. Rau, and T. Kirchartz, "Relevance of long diffusion lengths for efficient halide perovskite solar cells," *PRX Energy*, vol. 2, no. 1, p. 013004, 2023.
- [77] S. P. Senanayak *et al.*, "Charge transport in mixed metal halide perovskite semiconductors," *Nature Materials*, vol. 22, no. 2, p. 216-224, 2023.
- [78] J. Kim, A. J. Yun, B. Park, and J. Kim, "Recent progress in carbon electrodes for efficient and cost-benign perovskite optoelectronics," *Electronic Materials Letters*, vol. 18, no. 3, p. 232-255, 2022.
- [79] J. Liu, T. Ye, D. Yu, S. Liu, and D. Yang, "Recoverable Flexible Perovskite Solar Cells for Next-Generation Portable Power Sources," *Angewandte Chemie*, vol. 135, no. 40, p. e202307225, 2023.
- [80] S. S. Kahandal *et al.*, "Perovskite Solar Cells: Fundamental Aspects, Stability Challenges, and Future Prospects," *Progress in Solid State Chemistry*, vol. 74, p. 100463, 2024.
- [81] X. Yu *et al.*, "Numerical simulation analysis of effect of energy band alignment and functional layer thickness on the performance for perovskite solar cells with $\text{Cd}_{1-x}\text{Zn}_x\text{S}$ electron transport layer," *Materials Research Express*, vol. 7, no. 10, p. 105906, 2020.
- [82] Y. Huang *et al.*, "Towards simplifying the device structure of high-performance perovskite solar cells," *Advanced Functional Materials*, vol. 30, no. 28, p. 2000863, 2020.
- [83] N. G. Park, "Towards Stable, 30% Efficient Perovskite Solar Cells," *Korean Journal of Chemical Engineering*, vol. 41, p. 1-12, 2024.
- [84] C. Zhang *et al.*, "Work function tuning of a weak adhesion homojunction for stable perovskite solar cells," *Joule*, vol. 8, no. 5, p. 1394-1411, 2024.
- [85] B. Wang *et al.*, "The charge carrier dynamics, efficiency and stability of two-dimensional material-based perovskite solar cells," *Chemical Society Reviews*, vol. 48, no. 18, p. 4854-4891, 2019.
- [86] J. Xia, M. Sohail, and M. K. Nazeeruddin, "Efficient and stable perovskite solar cells by tailoring of interfaces," *Advanced Materials*, vol. 35, no. 31, p. 2211324, 2023.
- [87] H. Zhang and N.-G. Park, "Progress and issues in pin type perovskite solar cells," *DeCarbon*, vol. 3, p. 100025, 2024.

- [88] Y. Pu, H. Su, C. Liu, M. Guo, L. Liu, and H. Fu, "A review on buried interface of perovskite solar cells," *Energies*, vol. 16, no. 13, p. 5015, 2023.
- [89] G. J. Aalbers, T. P. van der Pol, K. Datta, W. H. Remmerswaal, M. M. Wienk, and R. A. Janssen, "Effect of sub-bandgap defects on radiative and non-radiative open-circuit voltage losses in perovskite solar cells," *Nature Communications*, vol. 15, no. 1, p. 1276, 2024.
- [90] R. Hidayat *et al.*, "Revealing the charge carrier kinetics in perovskite solar cells affected by mesoscopic structures and defect states from simple transient photovoltage measurements," *Scientific Reports*, vol. 10, no. 1, p. 19197, 2020.
- [91] H. Wang *et al.*, "Photomechanically accelerated degradation of perovskite solar cells," *Energy & Environmental Science*, vol. 18, no. 5, p. 2254-2263, 2025.
- [92] L. Hu *et al.*, "Doping of ZnO Electron Transport Layer with Organic Dye Molecules to Enhance Efficiency and Photo-Stability of the Non-Fullerene Organic Solar Cells," *Small*, vol. 20, no. 21, p. 2310125, 2024.
- [93] Y. Yu, J. Xia, and Y. Liang, "Basic understanding of perovskite solar cells and passivation mechanism," *AIP Advances*, vol. 12, no. 5, 2022.
- [94] P. Zhao, B. J. Kim, and H. S. Jung, "Passivation in perovskite solar cells: A review," *Materials Today Energy*, vol. 7, p. 267-286, 2018.
- [95] L. Wan *et al.*, "Efficient light harvesting with a nanostructured organic electron-transporting layer in perovskite solar cells," *Nanoscale*, vol. 11, no. 19, p. 9281-9286, 2019.
- [96] F. Rehman *et al.*, "Fourth-generation solar cells: a review," *Energy Advances*, vol. 2, no. 9, p. 1239-1262, 2023.
- [97] N. K. Singh and A. Agarwal, "Performance assessment of sustainable highly efficient CsSn_{0.5}Ge_{0.5}I₃/FASnI₃ based Perovskite Solar Cell: A numerical modelling approach," *Optical Materials*, vol. 139, p. 113822, 2023.
- [98] F. Pakraves and M. Izadyar, "Molecular engineering of inorganic halide perovskites and HTMs for photovoltaic applications," *International Journal of Quantum Chemistry*, vol. 124, no. 1, p. e27239, 2024.
- [99] E. F. Sawires *et al.*, "Exploring various Integration Methods of carbon quantum dots in CsPbCl₃ perovskite solar cells for enhanced power conversion efficiency," *Journal of Materials Science: Materials in Electronics*, vol. 35, no. 11, p. 1-16, 2024.
- [100] S. S. Birajdar, K. Bhardwaj, R. Kumar, M. Al Kobaisi, S. V. Bhosale, and S. V. Bhosale, "An efficient electron transport properties of fullerene functionalized with tricyanovinylidihydrofuran (TCF)," *Materials Research Bulletin*, vol. 147, p. 111644, 2022.
- [101] A. H. H. Khan and Y. C. Wang, "Tailoring transporters for all-inorganic tin-based perovskite solar cells with efficiency exceeding 22% using SCAPS-1D simulator," *Inorganic Chemistry Communications*, vol. 179, p. 114707, 2025.
- [102] H. Khan and M. U. H. Shah, "Modification strategies of TiO₂ based photocatalysts for enhanced visible light activity and energy storage ability: A Review," *Journal of Environmental Chemical Engineering*, vol. 11, p. 111532, 2023.
- [103] Y. Sari, P. L. Gareso, B. Arminah, and D. Tahir, "A review of TiO₂ photocatalyst for organic degradation and sustainable hydrogen energy production," *International Journal of Hydrogen Energy*, vol. 55, p. 984-996, 2023.
- [104] A. K. Chakraborty, S. Ganguli, and M. A. Sabur, "Nitrogen doped titanium dioxide (N-TiO₂): Electronic band structure, visible light harvesting and photocatalytic applications," *Journal of Water Process Engineering*, vol. 55, p. 104183, 2023.

- [105] S. Gouthaman and K. J. Thomas, "Metal Oxide Nanostructures as an Electron Transport Layer for Dye-Sensitized Solar Cells," in *Optical Properties of Metal Oxide Nanostructures*: Springer, vol. 1, p. 223-262, 2023.
- [106] F. V. Maziviero *et al.*, "Advancements and Prospects in Perovskite Solar Cells: From Hybrid to All-Inorganic Materials," *Nanomaterials*, vol. 14, no. 4, p. 332, 2024.
- [107] K. Kato, N. Nagatsuka, and K. Fukutani, "H₂ Molecule Generation from Dissociatively Adsorbed Water on TiO₂ through Photoexcitation," *The Journal of Physical Chemistry C*, vol.128, no. 20, p. 8188-8198, 2024.
- [108] N. A. Z. Abidin *et al.*, "Dopant engineering for ZnO electron transport layer towards efficient perovskite solar cells," *RSC Advances*, vol. 13, no. 48, p. 33797-33819, 2023.
- [109] C. Qiu, Y. Wu, J. Song, W. Wang, and Z. Li, "Efficient planar perovskite solar cells with ZnO electron transport layer," *Coatings*, vol. 12, no. 12, p. 1981, 2022.
- [110] L. Derbali, F. Bouhjar, A. Derbali, and B. Soucase, "Enhanced ZnO-based ETL and nanostructured interface modification for improved perovskite solar cells efficiency," *Optical Materials*, vol. 145, p. 114440, 2023.
- [111] F. Behrouznejad *et al.*, "Modification of copper-based chalcogenide nanocrystals' interconnections for efficient hole transportation in Perovskite solar cell," *Materials Research Bulletin*, vol. 178, p. 112892, 2024.
- [112] L. Zang, C. Zhao, X. Hu, J. Tao, S. Chen, and J. Chu, "Emerging Trends in Electron Transport Layer Development for Stable and Efficient Perovskite Solar Cells," *Small*, vol. 20, no. 26, p. 2400807, 2024.
- [113] A. Ghosh *et al.*, "Improving the power conversion efficiency of RbPbBr₃ absorber based solar cells through the variation of efficient hole transport layers," *Journal of Physics and Chemistry of Solids*, vol. 193, p. 112179, 2024.
- [114] D. Stock, N. Weinberger, F. Ruske, L. Haug, M. Harnisch, and R. Lackner, "Development of direct current magnetron sputtered TiO_{2-x} thin films as buffer layers for copper indium gallium diselenide based solar cells," *Thin Solid Films*, vol. 786, p. 140115, 2023.
- [115] B. K. Mohammed, M. K. Mohammed, and D. S. Ahmed, "Efficient planar mixed-cation perovskite photovoltaics with low-temperature-processed indium sulfide as electron transport material," *Solid-State Electronics*, vol. 204, p. 108640, 2023.
- [116] S. Ijaz *et al.*, "Numerical simulation to optimize the efficiency of HTM-free perovskite solar cells by ETM engineering," *Solar Energy*, vol. 250, p. 108-118, 2023.
- [117] V. P. Hoang Huy, T. M. H. Nguyen, and C. W. Bark, "Recent Advances of Doped SnO₂ as Electron Transport Layer for High-Performance Perovskite Solar Cells," *Materials*, vol. 16, no. 18, p. 6170, 2023.
- [118] B. Yang, S. Peng, and W. C. Choy, "Inorganic top electron transport layer for high performance inverted perovskite solar cells," *EcoMat*, vol. 3, no. 5, p. e12127, 2021.
- [119] V. P. Hoang Huy and C. W. Bark, "Review on surface modification of SnO₂ electron transport layer for high-efficiency perovskite solar cells," *Applied Sciences*, vol. 13, no. 19, p. 10715, 2023.
- [120] Y. Wang, J. Wan, J. Ding, J. S. Hu, and D. Wang, "A rutile TiO₂ electron transport layer for the enhancement of charge collection for efficient perovskite solar cells," *Angewandte Chemie International Edition*, vol. 58, no. 28, p. 9414-9418, 2019.
- [121] B. Xu *et al.*, "Recent Progress on Cross-Linkable Fullerene-based Electron Transport Materials for Perovskite Solar Cells," *ChemSusChem*, vol. 18, no. 3, p. e202401629, 2025.

- [122] S. Zhang *et al.*, "Barrier designs in perovskite solar cells for long-term stability," *Advanced Energy Materials*, vol. 10, no. 35, p. 2001610, 2020.
- [123] J. Wei *et al.*, "Mechanisms and suppression of photoinduced degradation in perovskite solar cells," *Advanced Energy Materials*, vol. 11, no. 3, p. 2002326, 2021.
- [124] S. M. Hassan, A. I. Ahmed, and M. A. Mannaa, "Structural, photocatalytic, biological and catalytic properties of SnO₂/TiO₂ nanoparticles," *Ceramics International*, vol. 44, no. 6, p. 6201-6211, 2018.
- [125] S. U. Rehman, S. Musuvadhi Babulal, D. Dabur, and H.-F. Wu, "Hierarchically Designed Polydopamine@ Co₃O₄-SnO₂-Anchored Cellulose Photothermal Sponge for Efficient Interfacial Solar Steam Generation," *ACS ES&T Water*, vol. 4, no. 1, p. 134-145, 2023.
- [126] M. Muzakir *et al.*, "Inorganic solid electrolytes for all-solid-state sodium/lithium-ion batteries: recent development and applications," *Journal of Materials Chemistry A*, vol.13, no. 1, p. 5, 2024.
- [127] G. K. Dalapati *et al.*, "Tin oxide for optoelectronic, photovoltaic and energy storage devices: a review," *Journal of Materials Chemistry A*, vol. 9, no. 31, p. 16621-16684, 2021.
- [128] P. C. Huang *et al.*, "Visualizing band alignment across 2D/3D perovskite heterointerfaces of solar cells with light-modulated scanning tunneling microscopy," *Nano Energy*, vol. 89, p. 106362, 2021.
- [129] Y. C. Wang, X. Li, L. Zhu, X. Liu, W. Zhang, and J. Fang, "Efficient and hysteresis-free perovskite solar cells based on a solution processable polar fullerene electron transport layer," *Advanced Energy Materials*, vol. 7, no. 21, p. 1701144, 2017.
- [130] Y. Gao *et al.*, "Flexible perovskite solar cells: From materials and device architectures to applications," *ACS Energy Letters*, vol. 7, no. 4, p. 1412-1445, 2022.
- [131] J. Liu, L. Qiu, and S. Shao, "Emerging electronic applications of fullerene derivatives: an era beyond OPV," *Journal of Materials Chemistry C*, vol. 9, no. 45, p. 16143-16163, 2021.
- [132] H. Wang, C. Zhang, Y. Yao, C. Cheng, and K. Wang, "Non-Fullerene Organic Electron Transport Materials toward Stable and Efficient Inverted Perovskite Photovoltaics," *Small*, vol. 20, no. 43, p. 2403193, 2024.
- [133] A. Islam, K. Usman, Z. Haider, M. F. Alam, A. Nawaz, and P. Sonar, "Biomass-Derived Materials for Interface Engineering in Organic/Perovskite Photovoltaic and Light-Emitting Devices," *Advanced Materials Technologies*, vol. 8, no. 7, p. 2201390, 2023.
- [134] S. Ge *et al.*, "A review on the progress of optoelectronic devices based on TiO₂ thin films and nanomaterials," *Nanomaterials*, vol. 13, no. 7, p. 1141, 2023.
- [135] S. You *et al.*, "C₆₀-based ionic salt electron shuttle for high-performance inverted perovskite solar modules," *Science*, vol. 0, p. eadv4701, 2025.
- [136] A. V. Baskar *et al.*, "Self-assembled fullerene nanostructures: synthesis and applications," *Advanced Functional Materials*, vol. 32, no. 6, p. 2106924, 2022.
- [137] K. Feng *et al.*, "Non-fullerene electron-transporting materials for high-performance and stable perovskite solar cells," *Nature Materials*, vol. 24, p. 770-777, 2025.
- [138] C. Lee, Y. Seo, J. Han, J. Hwang, and I. Jeon, "Perspectives on critical properties of fullerene derivatives for rechargeable battery applications," *Carbon*, vol. 210, p. 118041, 2023.
- [139] X. Yin, Z. Wang, Y. Zhao, S. Zhang, Y. Zhang, and Y. Song, "Cross-linking polymerization boosts the performance of perovskite solar cells: from material design to performance regulation," *Energy & Environmental Science*, vol. 16, no. 10, p. 4251-4279, 2023.

- [140] M. Ai, M. Chen, and S. Yang, "Recent Advances in Functionalized Fullerenes in Perovskite Solar Cells," *Chinese Journal of Chemistry*, vol. 41, no. 18, p. 2337-2353, 2023.
- [141] Y. C. Wang, J. Chang, L. Zhu, X. Li, C. Song, and J. Fang, "Electron-transport-layer-assisted crystallization of perovskite films for high-efficiency planar heterojunction solar cells," *Advanced Functional Materials*, vol. 28, no. 9, p. 1706317, 2018.
- [142] Z. Xing, S.-H. Li, and S. Yang, "Targeted molecular design of functionalized fullerenes for high-performance and stable perovskite solar cells," *Small Structures*, vol. 3, no. 6, p. 2200012, 2022.
- [143] T. Cao *et al.*, "Interfacial engineering via inserting functionalized water-soluble fullerene derivative interlayers for enhancing the performance of perovskite solar cells," *Journal of Materials Chemistry A*, vol. 6, no. 8, p. 3435-3443, 2018.
- [144] J. Chang, Y.-C. Wang, C. Song, L. Zhu, Q. Guo, and J. Fang, "Carboxylic ester-terminated fulleropyrrolidine as an efficient electron transport material for inverted perovskite solar cells," *Journal of Materials Chemistry C*, vol. 6, no. 26, p. 6982-6987, 2018.
- [145] Z. Saki *et al.*, "The synergistic effect of dimethyl sulfoxide vapor treatment and C₆₀ electron transporting layer towards enhancing current collection in mixed-ion inverted perovskite solar cells," *Journal of Power Sources*, vol. 405, p. 70-79, 2018.
- [146] A. R. bin Mohd Yusoff, M. Vasilopoulou, D. G. Georgiadou, L. C. Palilis, A. Abate, and M. K. Nazeeruddin, "Passivation and process engineering approaches of halide perovskite films for high efficiency and stability perovskite solar cells," *Energy & Environmental Science*, vol. 14, no. 5, p. 2906-2953, 2021.
- [147] Q.-J. Shui *et al.*, "Evaporable fullerene indanones with controlled amorphous morphology as electron transport layers for inverted perovskite solar cells," *Journal of the American Chemical Society*, vol. 145, no. 50, p. 27307-27315, 2023.
- [148] C. Tian *et al.*, "Fullerene derivative with flexible alkyl chain for efficient tin-based perovskite solar cells," *Nanomaterials*, vol. 12, no. 3, p. 532, 2022.
- [149] A. D. Khan *et al.*, "Advancements in the stability, protection and lead-free strategies of perovskite solar cells: a critical review," *Environmental Science Advances*, vol. 3, no. 7, p. 1004-1029, 2024.
- [150] P. Guo *et al.*, "Surface & grain boundary co-passivation by fluorocarbon based bifunctional molecules for perovskite solar cells with efficiency over 21%," *Journal of Materials Chemistry A*, vol. 7, no. 6, p. 2497-2506, 2019.
- [151] C. Tian *et al.*, "Fullerene derivative with a branched alkyl chain exhibits enhanced charge extraction and stability in inverted planar perovskite solar cells," *New Journal of Chemistry*, vol. 42, no. 4, p. 2896-2902, 2018.
- [152] W. Zhang *et al.*, "Strategies for improving efficiency and stability of inverted perovskite solar cells," *Advanced Materials*, vol. 36, no. 37, p. 2311025, 2024.
- [153] M. Bouachrine, N. Belghiti, M. Nassiri Bennani, S. Bouzzine, and M. Hamidi, "The DFT chemical investigations of optoelectronic and photovoltaic properties of short-chain conjugated molecules," *Physical Chemistry Research*, vol. 2, no. 1, p. 11-20, 2014.
- [154] L. Jia, M. Chen, and S. Yang, "Functionalization of fullerene materials toward applications in perovskite solar cells," *Materials Chemistry Frontiers*, vol. 4, no. 8, p. 2256-2282, 2020.
- [155] O. Fernandez-Delgado *et al.*, "Variation of interfacial interactions in PCBM-like electron-transporting compounds for perovskite solar cells," *ACS Applied Materials & Interfaces*, vol. 11, no. 37, p. 34408-34415, 2019.

- [156] K. Wojciechowski *et al.*, "Cross-linkable fullerene derivatives for solution-processed n-i-p perovskite solar cells," *ACS Energy Letters*, vol. 1, no. 4, p. 648-653, 2016.
- [157] Y. Dong *et al.*, "Highly efficient planar perovskite solar cells via interfacial modification with fullerene derivatives," *Small*, vol. 12, no. 8, p. 1098-1104, 2016.
- [158] X. Liu, M. Lei, Y. Zhou, B. Song, and Y. Li, "High performance planar pin perovskite solar cells with crown-ether functionalized fullerene and LiF as double cathode buffer layers," *Applied Physics Letters*, vol. 107, no. 6, p. 063901, 2015.
- [159] S. Li *et al.*, "Unravelling the mechanism of ionic fullerene passivation for efficient and stable methylammonium-free perovskite solar cells," *ACS Energy Letters*, vol. 5, no. 6, p. 2015-2022, 2020.
- [160] B. L. Watson, N. Rolston, K. A. Bush, T. Leijtens, M. D. McGehee, and R. H. Dauskardt, "Cross-linkable, solvent-resistant fullerene contacts for robust and efficient perovskite solar cells with increased J_{sc} and V_{oc} ," *ACS Applied Materials & Interfaces*, vol. 8, no. 39, p. 25896-25904, 2016.
- [161] B. Li *et al.*, "Steering the electron transport properties of pyridine-functionalized fullerene derivatives in inverted perovskite solar cells: The nitrogen site matters," *Journal of Materials Chemistry A*, vol. 8, no. 7, p. 3872-3881, 2020.
- [162] R. Lin *et al.*, "Monolithic all-perovskite tandem solar cells with 24.8% efficiency exploiting comproportionation to suppress Sn (ii) oxidation in precursor ink," *Nature Energy*, vol. 4, no. 10, p. 864-873, 2019.
- [163] K. Yan *et al.*, "A multifunctional and scalable fullerene electron transporting material for efficient inverted perovskite solar cells and modules," *Science China Chemistry*, vol. 66, no. 6, p. 1795-1803, 2023.
- [164] S. V. Bhosale, M. Al Kobaisi, R. W. Jadhav, P. P. Morajkar, L. A. Jones, and S. George, "Naphthalene diimides: perspectives and promise," *Chemical Society Reviews*, vol. 50, no. 17, p. 9845-9998, 2021.
- [165] Q. Chen, W. Wang, S. Xiao, Y.-B. Cheng, F. Huang and W. Xiang, "Improved performance of planar perovskite solar cells using an amino-terminated multifunctional fullerene derivative as the passivation layer," *ACS Applied Materials & Interfaces*, vol. 11, no. 30, p. 27145-27152, 2019.
- [166] M. Zhang *et al.*, "Reconfiguration of interfacial energy band structure for high-performance inverted structure perovskite solar cells," *Nature Communications*, vol. 10, no. 1, p. 4593, 2019.
- [167] L. Jia, B. Li, Y. Shang, M. Chen, G.-W. Wang, and S. Yang, "Double fullerene cathode buffer layers afford highly efficient and stable inverted planar perovskite solar cells," *Organic Electronics*, vol. 82, p. 105726, 2020.
- [168] Q. Chen, C. Wang, Y. Li, and L. Chen, "Interfacial dipole in organic and perovskite solar cells," *Journal of the American Chemical Society*, vol. 142, no. 43, p. 18281-18292, 2020.
- [169] E. Voroshazi *et al.*, "Novel bis-C₆₀ derivative compared to other fullerene bis-adducts in high efficiency polymer photovoltaic cells," *Journal of Materials Chemistry*, vol. 21, no. 43, p. 17345-17352, 2011.
- [170] Y. Xing, C. Sun, H.-L. Yip, G. C. Bazan, F. Huang, and Y. Cao, "New fullerene design enables efficient passivation of surface traps in high performance pin heterojunction perovskite solar cells," *Nano Energy*, vol. 26, p. 7-15, 2016.

- [171] Z. Zhu, C. C. Chueh, F. Lin, and A. K. Y. Jen, "Enhanced ambient stability of efficient perovskite solar cells by employing a modified fullerene cathode interlayer," *Advanced Science*, vol. 3, no. 9, p. 1600027, 2016.
- [172] J. Xie *et al.*, "Improved performance and air stability of planar perovskite solar cells via interfacial engineering using a fullerene amine interlayer," *Nano Energy*, vol. 28, p. 330-337, 2016.
- [173] S.-K. Huang *et al.*, "Unravelling the origin of the photocarrier dynamics of fullerene-derivative passivation of SnO₂ electron transporters in perovskite solar cells," *Journal of Materials Chemistry A*, vol. 8, no. 44, p. 23607-23616, 2020.
- [174] H.-J. Yu *et al.*, "Light-soaking effects and capacitance profiling in Cu (In, Ga) Se₂ thin-film solar cells with chemical-bath-deposited ZnS buffer layers," *Physical Chemistry Chemical Physics*, vol. 18, no. 48, p. 33211-33217, 2016.
- [175] A. Soultati *et al.*, "Interfacial engineering for organic and perovskite solar cells using molecular materials," *Journal of Physics D: Applied Physics*, vol. 53, no. 26, p. 263001, 2020.
- [176] Z. Xing *et al.*, "Multifunctional molecular design of a new fulleropyrrolidine electron transport material family engenders high performance of perovskite solar cells," *Advanced Functional Materials*, vol. 31, no. 51, p. 2107695, 2021.
- [177] N. Cates *et al.*, "Molecular packing and solar cell performance in blends of polymers with a bisadduct fullerene," *Nano Letters*, vol. 12, no. 3, p. 1566-1570, 2012.
- [178] M. Vasilopoulou *et al.*, "Molecular materials as interfacial layers and additives in perovskite solar cells," *Chemical Society Reviews*, vol. 49, no. 13, p. 4496-4526, 2020.
- [179] Y. Wang *et al.*, "Pyridine-functionalized fullerene derivative as an independent electron transport layer enabling efficient and hysteresis-free regular perovskite solar cells," *Nano Select*, vol. 2, no. 11, p. 2192-2200, 2021.
- [180] B. Li *et al.*, "Efficient and stable tin perovskite solar cells by pyridine-functionalized fullerene with reduced interfacial energy loss," *Advanced Functional Materials*, vol. 32, no. 39, p. 2205870, 2022.
- [181] B. Li *et al.*, "Anchoring fullerene onto perovskite film via grafting pyridine toward enhanced electron transport in high-efficiency solar cells," *ACS Applied Materials & Interfaces*, vol. 10, no. 38, p. 32471-32482, 2018.
- [182] H. Cheng, X. Zang, S. Wang, and B. Cai, "Pyridine-Functionalized Organic Molecules in Perovskite Solar Cells: Toward Defects Passivation and Charge Transfer," *Solar RRL*, vol. 9, no. 2, p. 2400736, 2025.
- [183] Y. Sun, Y. Lai, and Y. Yang, "Progress of Hole-Transport Layers in Mixed Sn-Pb Perovskite Solar Cells," *Small*, vol. 20, no. 49, p. 2406991, 2024.
- [184] J. Zhen *et al.*, "Pyridine-functionalized fullerene additive enabling coordination interactions with CH₃NH₃PbI₃ perovskite towards highly efficient bulk heterojunction solar cells," *Journal of Materials Chemistry A*, vol. 7, no. 6, p. 2754-2763, 2019.
- [185] B. Roy, T. Dey, S. Bose, S. Mahato, N. C. Das, and S. K. Ray, "Superior Photoconversion Efficiency of Nanocrystal Sensitized Solar Cells Based on All-Inorganic CsPbX₃ (X= Br, I) Perovskites," *Nanoscale*, vol. 17, p. 10743-10751, 2025.
- [186] S. Wang *et al.*, "Targeted therapy for interfacial engineering toward stable and efficient perovskite solar cells," *Advanced Materials*, vol. 31, no. 41, p. 1903691, 2019.

- [187] L. L. Deng, S. Y. Xie, and F. Gao, "Fullerene-Based Materials for Photovoltaic Applications: Toward Efficient, Hysteresis-Free, and Stable Perovskite Solar Cells," *Advanced Electronic Materials*, vol. 4, no. 10, p. 1700435, 2018.
- [188] J. Li, M. Chen, S. Zhou, H. Li, and J. Hao, "Self-assembly of fullerene C₆₀-based amphiphiles in solutions," *Chemical Society Reviews*, vol. 51, no. 8, p. 3226-3242, 2022.
- [189] X. Tong *et al.*, "Synergistically manipulating the shape of alkyl-chain and asymmetric side groups of non-fullerene acceptors enables organic solar cells to reach 18.5% efficiency," *Giant*, vol. 19, p. 100294, 2024.
- [190] Y. C. Wang *et al.*, "Terpyridine-zinc (ii) coordination nanosheets as modulators of perovskite crystallization to enhance solar cell efficiency," *Journal of Materials Chemistry A*, vol. 11, no. 13, p. 7077-7084, 2023.
- [191] D. Yadav *et al.*, "Stimuli-responsive biomaterials for tissue engineering applications," *Current Pharmaceutical Biotechnology*, vol. 25, no. 8, p. 981-999, 2024.
- [192] D. M. Guldi, G. A. Rahman, V. Sgobba, and C. Ehli, "Multifunctional molecular carbon materials—from fullerenes to carbon nanotubes," *Chemical Society Reviews*, vol. 35, no. 5, p. 471-487, 2006.
- [193] H. Wang *et al.*, "Halogen-substituted fullerene derivatives for interface engineering of perovskite solar cells," *Journal of Materials Chemistry A*, vol. 6, no. 43, p. 21368-21378, 2018.
- [194] S. Hu, J. Thiesbrummel, J. Pascual, M. Stolterfoht, A. Wakamiya, and H. J. Snaith, "Narrow Bandgap Metal Halide Perovskites for All-Perovskite Tandem Photovoltaics," *Chemical Reviews*, vol. 124, no. 7, p. 4079-4123, 2024.
- [195] L. Hong *et al.*, "Simultaneous improvement of efficiency and stability of organic photovoltaic cells by using a cross-linkable fullerene derivative," *Small*, vol. 17, no. 24, p. 2101133, 2021.
- [196] T. Kang *et al.*, "Interfacial engineering with cross-linkable fullerene derivatives for high-performance perovskite solar cells," *ACS Applied Materials & Interfaces*, vol. 9, no. 44, p. 38530-38536, 2017.
- [197] F. Giacalone and N. Martín, "New concepts and applications in the macromolecular chemistry of fullerenes," *Advanced Materials*, vol. 22, no. 38, p. 4220-4248, 2010.
- [198] Y. Wang, X. Wang, Z. Ding, Y. Wang, and W. Huang, "Cross-linking strategies for efficient and highly stable perovskite solar cells," *Journal of Materials Chemistry C*, vol. 12, p. 351-387, 2023.
- [199] A. Cabrera-Espinoza, S. Collavini, J. G. Sánchez, I. Kosta, E. Palomares, and J. L. Delgado, "Photo-Cross-Linked Fullerene-Based Hole Transport Material for Moisture-Resistant Regular Fullerene Sandwich Perovskite Solar Cells," *ACS Applied Materials & Interfaces*, vol. 16, no. 16, p. 20852-20864, 2024.
- [200] A. Diacon, L. Derue, C. Lecourtier, O. Dautel, G. Wantz, and P. Hudhomme, "Cross-linkable azido C₆₀-fullerene derivatives for efficient thermal stabilization of polymer bulk-heterojunction solar cells," *Journal of Materials Chemistry C*, vol. 2, no. 35, p. 7163-7167, 2014.
- [201] D. A. García-Hernández, R. Barzaga, A. Manchado, and F. Cataldo, "Fullerene-indene adducts (ICMA & ICBA) in an astrochemical perspective part 1: chemical thermodynamics, stability and electronic absorption spectroscopy," *Fullerenes, Nanotubes and Carbon Nanostructures*, vol. 31, no. 9, p. 897-905, 2023.

- [202] R. M. Faisal, "Buckyball Derivatives as Acceptors in Organic Photovoltaics: A Review." vol. 13, no. 1, p. 119-149, 2022.
- [203] Y. Shi, Z. Zhu, D. Miao, Y. Ding, and Q. Mi, "Interfacial Dipoles Boost Open-Circuit Voltage of Tin Halide Perovskite Solar Cells," *ACS Energy Letters*, vol. 9, no. 4, p. 1895-1897, 2024.
- [204] T. Ji *et al.*, "Charge transporting materials for perovskite solar cells," *Rare Metals*, vol. 40, no. 10, p. 2690-2711, 2021.
- [205] B. Ali, F. Almyahi, and M. A. Mahdi, "Effect of Poly (3-Hexylthiophene): Mixed Fullerene Indene-C₆₀ Multi-Adducts Ratios on the Performance of Organic Solar Cells," *Iranian Journal of Materials Science & Engineering*, vol. 20, no. 2, 2023.
- [206] J. Marin-Beloqui *et al.*, "Insight into the origin of trapping in polymer/fullerene blends with a systematic alteration of the fullerene to higher adducts," *The Journal of Physical Chemistry C*, vol. 126, no. 5, p. 2708-2719, 2022.
- [207] J. Qiu and S. Yang, "Material and Interface Engineering for High-Performance Perovskite Solar Cells: A Personal Journey and Perspective," *The Chemical Record*, vol. 20, no. 3, p. 209-229, 2020.
- [208] Y. Xie, H. Lu, J. Huang, and H. Xie, "Natural materials for sustainable organic solar cells: status and challenge," *Advanced Functional Materials*, vol. 33, no. 15, p. 2213910, 2023.
- [209] Y. Li, S. Yang, S. Yan, X. Liu, G. Shi, and T. He, "Open-Circuit Voltage Loss Management for Efficient Inverted Wide-Bandgap Perovskite Photovoltaics," *Advanced Functional Materials*, vol. 35, no. 7, p. 2415331, 2025.